



Microstructure and thickening of dense suspensions under extensional and shear flows

Ryohei Seto^{1,†}, Giulio G. Giusteri¹ and Antonio Martiniello¹

¹Mathematical Soft Matter Unit, Okinawa Institute of Science and Technology Graduate University, 1919-1 Tancha, Onna, Okinawa, 904-0495, Japan

(Received 7 June 2017; revised 28 June 2017; accepted 2 July 2017; first published online 27 July 2017)

Dense suspensions are non-Newtonian fluids that exhibit strong shear thickening and normal stress differences. Using numerical simulation of extensional and shear flows, we investigate how rheological properties are determined by the microstructure that is built under flows and by the interactions between particles. By imposing extensional and shear flows, we can assess the degree of flow-type dependence in regimes below and above thickening. Even when the flow-type dependence is hindered, non-dissipative responses, such as normal stress differences, are present and characterise the non-Newtonian behaviour of dense suspensions.

Key words: rheology, Stokesian dynamics, suspensions

1. Introduction

Suspensions, namely mixtures of solid particles and viscous liquids, can be considered as incompressible fluids as long as the volume fraction ϕ of solid particles is less than a certain value, the jamming point, above which a solid-like behaviour is observed. The behaviour of suspensions is not usually captured by simple Newtonian models. As a primary example of a non-Newtonian effect, the viscosity can vary with the shear rate, exhibiting shear thinning and shear thickening (Laun 1984; Barnes 1989; Bender & Wagner 1996; Guy, Hermes & Poon 2015). Moreover, non-vanishing normal stress differences N_1 and N_2 , further hallmarks of non-Newtonian behaviour, are often observed (Laun 1994; Lootens *et al.* 2005; Lee *et al.* 2006; Couturier *et al.* 2011; Dbouk, Lobry & Lemaire 2013; Cwalina & Wagner 2014). Discontinuous shear thickening is a particularly intriguing phenomenon of dense suspensions, and the underlying mechanism has raised significant debate (Brady & Bossis 1985; Hoffman 1998; Melrose & Ball 2004; Fall *et al.* 2008; Brown & Jaeger 2009). Analysis of the rheology of suspensions is a difficult task since forces of various types act among particles and the system lives mostly far from thermodynamic equilibrium.

[†] Email address for correspondence: setoryohei@me.com

Particle simulations have been used to explore the microstructure emerging among particles in various flows and to estimate the importance of different interactions. Several particle simulations have recently succeeded in reproducing shear thickening by taking into account direct contact forces (Fernandez *et al.* 2013; Heussinger 2013; Seto *et al.* 2013). These works support the ‘stress-induced friction’ scenario (Mari *et al.* 2014; Wyart & Cates 2014), and the contribution of contact forces was also confirmed in experiments (Lin *et al.* 2015; Clavaud *et al.* 2017). Thus, the particle-scale mechanism of shear thickening is, to a great extent, understood.

However, particle-scale simulations are not capable of reproducing engineering-scale flows of dense suspensions due to the practical limits imposed on the system size by computational tractability. For this reason, it is important to develop effective continuum models through the design of suitable non-Newtonian constitutive relations. Besides laboratory experiments, particle-scale simulations are an important source of indications for the development of such models. A complete model should describe the fluid response under any flow condition (Miller, Singh & Morris 2009), not only in the simple shear flows in which most experimental and computational data are retrieved. Indeed, the response of non-Newtonian fluids can depend on the type of flow, as exemplified by the observations of shear thinning and extensional thickening in some viscoelastic fluids. Particularly important is the class of extensional flows of suspensions, for which few rheological characterisations are available (Dai & Tanner 2017) and the sole computational investigation of which the authors are aware was performed by Sami (1996), who studied semidilute Brownian suspensions. (We note that in his analysis, flow-type dependence was not evidenced.) A related computational method to treat hydrodynamic interactions in diluted suspensions was introduced by Ahamadi & Harlen (2008). For important developments regarding emulsions of deformable droplets, we refer the reader to the work of Zinchenko & Davis (2015).

To study the material response, we simulate motions of particles in the bulk region under prescribed flow conditions. As usual, periodic boundary conditions are employed to minimise finite-size effects. The Lees–Edwards boundary conditions (Lees & Edwards 1972) are commonly used to impose simple shear flows in many contexts, including suspension rheology (Bossis & Brady 1984; Mari *et al.* 2014). In this work, we also apply the Kraynik–Reinelt boundary conditions (Kraynik & Reinelt 1992; Todd & Davis 1998), originally devised to impose planar extensional flows in non-equilibrium molecular dynamics simulations. With these, we can provide a first assessment of the flow-type dependence of the response in dense suspensions.

In §§ 2.1 and 2.2, we describe our simulation technique, which operates in the inertialess approximation. To compare the results under different flow conditions consistently, we employ the rheometric framework introduced by Giusteri & Seto (2017) (summarised in § 2.3), which defines, for the case of planar flows, a dissipative response function, κ , and two non-dissipative response functions, λ_0 and λ_3 . These are defined for any flow type (simple shear, extensional and mixed flows) and offer a unified description of the material response. The results of our analysis, discussed in § 3, highlight the presence of flow-type dependence in the microstructure and in the non-Newtonian effects observed for dense suspensions.

2. Methods

2.1. Bulk rheology with periodic boundary conditions

Non-Newtonian incompressible fluids obey the differential equations

$$\rho \left[\frac{\partial \mathbf{u}}{\partial t} + (\mathbf{u} \cdot \nabla) \mathbf{u} \right] = \nabla \cdot \boldsymbol{\sigma}, \quad \text{with } \nabla \cdot \mathbf{u} = 0, \quad (2.1)$$

Dense suspensions under extensional and shear flows

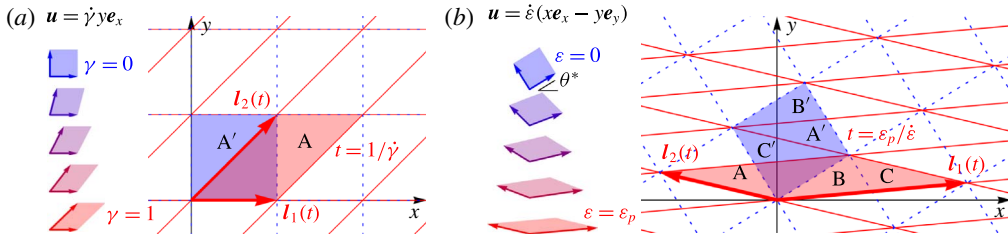


FIGURE 1. (a) The deforming periodic cells for simple shear flows. The initial rectangular shape can be recovered when the shear strain γ equals 1 by removing a part A of the master cell and including the corresponding part A' of a periodic image in the new master cell. It should be noted that the recovery can be performed at any value of the shear strain γ if the periodic displacement of the rows is taken into account. (b) The deforming periodic cells for extensional flow (Kraynik–Reinelt boundary conditions). The initial rectangular cell, which is oriented at a certain angle $\theta^* \approx 31.7^\circ$, can be recovered when the strain ϵ equals $\epsilon_p \approx 0.962$ by removing parts A–C of the master cell and including the corresponding parts A'–C' of periodic images in the new master cell.

where \mathbf{u} is the velocity field and ρ is the density. To close the system of equations, the stress tensor $\boldsymbol{\sigma}$ must be given in terms of the velocity gradient through a constitutive prescription. The local value of the stress tensor describes the material response and is determined by the local history of deformation. To investigate this response, we consider small volume elements in which the velocity gradient $\nabla\mathbf{u}$ is approximately uniform. By simulating motions of particles in the volume element with fixed $\nabla\mathbf{u}$, we can find the typical stress for a certain deformation history.

Time-dependent periodic boundary conditions allow us to impose $\nabla\mathbf{u}$ and effectively simulate the bulk behaviour. Since we consider planar flows in a 3D geometry, we can describe our methods considering the 2D projections of the computational cells. The cell frame vectors $\mathbf{l}_1(t)$ and $\mathbf{l}_2(t)$ (see figure 1) are prescribed to follow the velocity field $\mathbf{u} = \nabla\mathbf{u} \cdot \mathbf{r}$, and periodic images of a particle at \mathbf{r} are given by $\mathbf{r}' = \mathbf{r} + i\mathbf{l}_1(t) + j\mathbf{l}_2(t)$ with $(i, j = \pm 1, \pm 2, \dots)$. For simple shear flows ($\nabla\mathbf{u} = \dot{\gamma}\mathbf{e}_y\mathbf{e}_x$), this is equivalent to the Lees–Edwards boundary conditions. The initial periodic cells are rectangles in the flow plane (blue in figure 1a). A simple shear flow deforms the cells to parallelogram shapes (red in figure 1a). To avoid significantly deformed periodic cells, the initial rectangular cells can be recovered as shown in figure 1(a). To impose planar extensional flows ($\nabla\mathbf{u} = \dot{\epsilon}_x\mathbf{e}_x\mathbf{e}_x - \dot{\epsilon}_y\mathbf{e}_y\mathbf{e}_y$) for long times, we employ the Kraynik–Reinelt periodic boundary conditions (Kraynik & Reinelt 1992; Todd & Daivis 1998). If the initial master cell is a regular square oriented at a certain angle θ^* from the extension axis (x axis), the deformed parallelogram cell after a certain strain ϵ_p can be remapped to the initial regular shape, as shown in figure 1(b).

2.2. Inertialess particle dynamics for suspensions

We numerically evaluate the stress tensor $\boldsymbol{\sigma}$ by using particle simulations with deforming periodic cells. Our simulation is analogous to rate-controlled rheological measurements in the sense that time-averaged stress responses $\langle\boldsymbol{\sigma}\rangle$ are evaluated for imposed velocity gradients $\nabla\mathbf{u}$.

We consider non-Brownian, density matched and dense suspensions. Suspended particles interact with each other in several ways. As discussed in Mari *et al.* (2014), we take into account contact forces \mathbf{F}_C (and torques \mathbf{T}_C) and stabilising

repulsive forces \mathbf{F}_R , besides hydrodynamic interactions \mathbf{F}_H and \mathbf{T}_H . Since the inertia of sufficiently small particles is negligible in comparison with the hydrodynamic drag forces, the particles obey the quasi-static equations of motion

$$\mathbf{F}_H + \mathbf{F}_C + \mathbf{F}_R = \mathbf{0} \quad \text{and} \quad \mathbf{T}_H + \mathbf{T}_C = \mathbf{0}. \tag{2.2a,b}$$

Here, forces \mathbf{F} and torques \mathbf{T} represent the set of forces and torques for N particles. Flows around microscale particles are dominated by viscous dissipation, and the inertia of the fluid is negligible, so they are described by the Stokes equations. The imposed velocity gradient $\nabla \mathbf{u}$ gives the background flow via the velocity $\mathbf{u}(\mathbf{r})$, vorticity $\boldsymbol{\omega} \equiv \nabla \times \mathbf{u}$ and rate of deformation tensor \mathbf{D} such that $\nabla \mathbf{u} \cdot \mathbf{r} = \mathbf{D} \cdot \mathbf{r} + (\boldsymbol{\omega}/2) \times \mathbf{r}$. In this case, the hydrodynamic interactions can be expressed as the sum of linear resistances to the relative velocities $\Delta \mathbf{U}^{(i)} \equiv \mathbf{U}^{(i)} - \mathbf{u}(\mathbf{r}^{(i)})$, angular velocities $\Delta \boldsymbol{\Omega}^{(i)} \equiv \boldsymbol{\Omega}^{(i)} - \boldsymbol{\omega}/2$, for $i = 1, \dots, N$, and imposed deformation \mathbf{D} via

$$\begin{pmatrix} \mathbf{F}_H \\ \mathbf{T}_H \end{pmatrix} = -\mathbf{R} \cdot \begin{pmatrix} \Delta \mathbf{U} \\ \Delta \boldsymbol{\Omega} \end{pmatrix} + \mathbf{R}' : \mathbf{D}_N, \tag{2.3}$$

where $\Delta \mathbf{U}$ and $\Delta \boldsymbol{\Omega}$ represent the set of relative velocities for N particles, \mathbf{D}_N is block-diagonal with N copies of \mathbf{D} , and \mathbf{R} and \mathbf{R}' are resistance matrices, which can, in principle, be derived from the Stokes equations once the particle configurations are given. In dense suspensions, the long-range hydrodynamic interactions are screened by crowds of particles. Therefore, we may approximately construct the resistance matrices by including only the contributions of Stokes drag and lubrication forces.

In real suspensions, the lubrication singularity in \mathbf{F}_H is absent due to factors such as the surface roughness of particles – direct contacts are not forbidden. Hence, we include the contact interactions \mathbf{F}_C and \mathbf{T}_C in (2.2). The contact forces between solid particles depend on the nature of the particle surfaces. This is effectively encoded in the friction coefficient μ that enters a simple friction model. By denoting with F_C^n and F_C^t normal and tangential forces respectively, we prevent sliding if $F_C^t \leq \mu F_C^n$. The normal force depends on the overlap between particles through an effective elastic constant and the tangential force depends on the sliding displacement in a similar way. The details of the model employed are given in Mari *et al.* (2014).

The presence of the stabilising repulsive force \mathbf{F}_R in (2.2) generates the rate dependence of rheological properties in such suspensions. Indeed, while reaching the same strain, \mathbf{F}_R can work more to prevent particle contacts under lower deformation rates, but less under higher rates. As a result, the number of contacts depends on the rate of the imposed flow. In colloidal suspensions, Brownian forces may play a similar role, as discussed by Mari *et al.* (2015a).

The bulk stress tensor is obtained as

$$\boldsymbol{\sigma} = -p_0 \mathbf{I} + 2\eta_0 \mathbf{D} + V^{-1} \left(\sum_i \mathbf{S}_D^{(i)} + \sum_{i>j} \mathbf{S}_P^{(i,j)} \right), \tag{2.4}$$

where η_0 is the viscosity of the solvent, $\mathbf{S}_D^{(i)}$ is the stresslet on particle i due to \mathbf{D} , and $\mathbf{S}_P^{(i,j)}$ is the stresslet due to non-hydrodynamic interparticle forces between particles i and j (Mari *et al.* 2015b). It should be noted that, since the hydrostatic pressure p_0 is arbitrary, we set $p_0 = 0$. However, the last term in (2.4) is not traceless and thus contributes to the total pressure $p \equiv -(1/3)\text{Tr} \boldsymbol{\sigma}$.

2.3. General response functions for steady flows of non-Newtonian fluids

The stress σ is a tensorial quantity, and we need a procedure to extract the relevant information from it in terms of scalar quantities. We are interested in comparing the material response under different types of imposed flow conditions. For this reason, we need a framework in which it is possible to identify the dependence on the flow type of each independent non-Newtonian effect. To this end, we use the framework introduced by Giusteri & Seto (2017), in which the characteristic rate of the imposed flow is defined independently of the flow type and a complete set of response functions is given. These functions generalise to any flow-type standard quantities such as viscosity and normal stress differences.

The velocity gradient $\nabla \mathbf{u}$ is decomposed into symmetric and antisymmetric parts as $\nabla \mathbf{u} = \mathbf{D} + \mathbf{W}$. In the planar case, with $\mathbf{D} \neq \mathbf{0}$, we denote by $\dot{\epsilon}$ the largest eigenvalue of \mathbf{D} and express $\hat{\mathbf{D}} \equiv \mathbf{D}/\dot{\epsilon}$ and $\hat{\mathbf{W}} \equiv \mathbf{W}/\dot{\epsilon}$ on the basis of the eigenvectors $\hat{\mathbf{d}}_1$ and $\hat{\mathbf{d}}_2$ of \mathbf{D} (corresponding to the eigenvalues $\dot{\epsilon}$ and $-\dot{\epsilon}$) as follows:

$$\hat{\mathbf{D}} = \hat{\mathbf{d}}_1 \hat{\mathbf{d}}_1 - \hat{\mathbf{d}}_2 \hat{\mathbf{d}}_2, \quad \hat{\mathbf{W}} = \beta_3 (\hat{\mathbf{d}}_2 \hat{\mathbf{d}}_1 - \hat{\mathbf{d}}_1 \hat{\mathbf{d}}_2). \tag{2.5a,b}$$

The non-vanishing and positive rate $\dot{\epsilon} > 0$ is used to set the time scale of deformation in any flow type. With this definition, the standard rate $\dot{\gamma}$ for simple shear corresponds to the value $2\dot{\epsilon}$. The vorticity ω_z is represented by the dimensionless parameter β_3 through $\omega_z = 2\dot{\epsilon}\beta_3$. It should be noted that planar extensional flows are characterised by $\beta_3 = 0$ and simple shear flows by $\beta_3 = 1$.

A general representation of the stress tensor in planar flows is then given by

$$\sigma(\dot{\epsilon}, \beta_3) = -p(\dot{\epsilon}, \beta_3)\mathbf{I} + \dot{\epsilon}[\kappa(\dot{\epsilon}, \beta_3)\hat{\mathbf{D}} + \lambda_0(\dot{\epsilon}, \beta_3)\hat{\mathbf{E}} + \lambda_3(\dot{\epsilon}, \beta_3)\hat{\mathbf{G}}_3], \tag{2.6}$$

where $\hat{\mathbf{E}} \equiv -(1/2)(\hat{\mathbf{d}}_1 \hat{\mathbf{d}}_1 + \hat{\mathbf{d}}_2 \hat{\mathbf{d}}_2) + \hat{\mathbf{d}}_3 \hat{\mathbf{d}}_3$, $\hat{\mathbf{d}}_3$ is the eigenvector of \mathbf{D} orthogonal to the flow plane and $\hat{\mathbf{G}}_3 \equiv \hat{\mathbf{d}}_1 \hat{\mathbf{d}}_2 + \hat{\mathbf{d}}_2 \hat{\mathbf{d}}_1$ is introduced to complete an orthogonal basis for the space of symmetric tensors for planar flows. The functional dependence of κ , λ_0 and λ_3 on the two kinematical parameters $\dot{\epsilon}$ and β_3 needs to be determined to characterise the response in generic flows. We remark that the response functions κ , λ_0 and λ_3 can depend on any other quantity that characterises the system. For instance, in §3, we will also show their dependence on the volume fraction ϕ . The function κ is the only one to carry information about dissipation. We therefore refer to it as the dissipative response function, a generalised viscosity. The functions λ_0 and λ_3 carry information about non-dissipative responses, and we call them non-dissipative response functions. The presence of a non-vanishing λ_0 leaves the eigenvectors of the stress σ aligned with those of \mathbf{D} , as happens in Newtonian fluids, but gives a contribution to the stress in the form of a modified pressure that is isotropic in the flow plane but different in the direction normal to the flow plane. On the other hand, a non-vanishing λ_3 corresponds to a rotation of the eigenvectors of σ in the flow plane with respect to those of \mathbf{D} , determining the reorientation angle

$$\varphi \equiv \arctan \left[\lambda_3 / \left(\kappa + \sqrt{\kappa^2 + \lambda_3^2} \right) \right]. \tag{2.7}$$

For the sake of comparison, the shear viscosity η and normal stress differences N_1 and N_2 , defined for simple shear flows with $\beta_3 = 1$ as functions of $\dot{\gamma} = 2\dot{\epsilon}$, are given by

$$\eta(2\dot{\epsilon}) = \kappa(\dot{\epsilon}, 1)/2, \quad N_1(2\dot{\epsilon}) = -2\dot{\epsilon}\lambda_3(\dot{\epsilon}, 1) \quad \text{and} \quad N_2(2\dot{\epsilon}) = \dot{\epsilon}[\lambda_3(\dot{\epsilon}, 1) - (3/2)\lambda_0(\dot{\epsilon}, 1)]. \tag{2.8a-c}$$

Moreover, the extensional viscosity, defined for extensional flows with $\beta_3 = 0$, is given by $\eta_E(\dot{\epsilon}) = 2\kappa(\dot{\epsilon}, 0)$. Therefore, the Trouton ratio $\eta_E(\dot{\epsilon})/\eta(2\dot{\epsilon})$ equals 4 only if $\kappa(\dot{\epsilon}, 0) = \kappa(\dot{\epsilon}, 1)$.

We want to stress that, to arrive at (2.6), no *a priori* assumption is made on the list of quantities on which the material functions can depend. Hence, the stress tensor for any non-Newtonian fluid model under steady flow conditions can be expressed in the form (2.6). For example, since \mathbf{D}^2 in planar flows is a linear combination of \mathbf{I} and $\hat{\mathbf{E}}$, the class of Reiner–Rivlin fluids corresponds to choosing $\lambda_3 = 0$, and assuming κ and λ_0 to be independent of β_3 . Similarly, second-order fluids under steady shear flows would produce constant values of κ and λ_0 , and entail $\lambda_3 \propto \beta_3 \dot{\epsilon}$, since, under such flows, $\mathbf{W} \cdot \mathbf{D} - \mathbf{D} \cdot \mathbf{W} = \beta_3 \dot{\epsilon}^2 \hat{\mathbf{G}}_3$. A detailed discussion of the representation (2.6) and its relation to fluid models is given in Giusteri & Seto (2017).

3. Results

To obtain the numerical results, we mainly performed 50 independent 3D simulations with 2000 particles. The periodic cells were initially cuboids with ratio 5 : 5 : 1. We also performed some simulations with 4000 particles using double-sized cells (5 : 5 : 2) to confirm the absence of significant finite-size effects (data are not shown). Regarding the friction coefficient, we set $\mu = 1$, since it is the value that, in a previous paper (Mari *et al.* 2015a), was found to give good agreement with the experimental data by Cwalina & Wagner (2014). It is worth mentioning that Tanner & Dai (2016) showed that $\mu = 0.5$ gives better quantitative agreement with different experimental data. Nevertheless, such a fine tuning of μ is not necessary for our qualitative analysis.

The short-range repulsive force is given by $|\mathbf{F}_R| = F_R(0) \exp[-(r - 2a)/(0.02a)]$, with a the particle radius. A reference rate is set as $\dot{\epsilon}_0 \equiv F_R(0)/(12\pi\eta_0 a^2)$. To estimate the importance of the inertial effects, we can use the Stokes number, given by

$$St \equiv \frac{2\rho_p a^2 \dot{\epsilon}}{\eta_0} = \frac{\rho_p F_R(0)}{6\pi\eta_0^2} \frac{\dot{\epsilon}}{\dot{\epsilon}_0}, \tag{3.1}$$

with ρ_p the particle density. Hence, inertial effects can be neglected if $St \ll 1$; that is, when the ratio $\dot{\epsilon}/\dot{\epsilon}_0$ is much smaller than $6\pi\eta_0^2/\rho_p F_R(0)$. The preceding threshold determines, for each specific system, the region in which the rheology curves obtained with our simulations can be expected to be in agreement with real data.

3.1. Dissipative response function κ

For the case of monodisperse suspensions, the dissipative response function κ significantly increases with the rate $\dot{\epsilon}$ in both simple shear and extensional flows (figure 2). Not only shear thickening but also extensional thickening occurs. However, below thickening, there is a clear flow-type dependence. The value of κ in extensional flow is much higher than the value obtained in simple shear flow (the Trouton ratio is much larger than 4). On the other hand, above thickening, the values of κ in extensional and shear flows are almost indistinguishable (the Trouton ratio is very close to 4) and the flow-type dependence is hindered.

The significant discrepancy observed below thickening is due to shear-induced ordering, which can occur only in simple shear flows, as we confirm by analysing the pair distribution functions in § 3.4. Since the streamlines of a simple shear flow

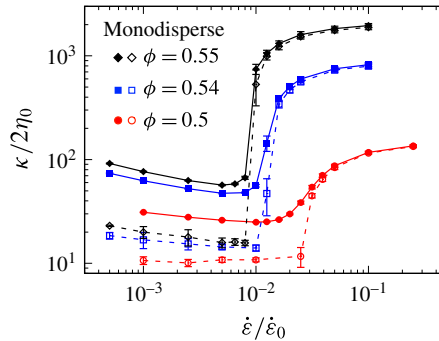


FIGURE 2. Both shear thickening and extensional thickening are observed in the rate dependence of the dissipative material function κ . The data are for monodisperse suspensions in extensional flows (filled symbols with solid lines) and in simple shear flows (open symbols with dashed lines). Below thickening, κ in simple shear flows is much lower than κ in extensional flows. In each simulation, the time average is taken over five strains after reaching the steady state. The error bars show the standard deviation for 50 independent simulations.

are straight and parallel to each other, particles tend to be arranged in chain-like structures along the flow direction. We observe a gradual decrease of κ over time (strain thinning) in simple shear flows, which indicates the growth of the ordered structure. It should be noted that the shear-induced ordering is enhanced by the periodic boundary conditions, since linear chains may connect with their own periodic images. By contrast, the streamlines of extensional flows are never parallel to each other. Therefore, there is no obvious ordered structure compatible with extensional flows. Indeed, we neither observe strain thinning nor any ordered microstructure in the extensional flow simulation.

In the thickened regime, frictional contact forces are constantly activated. These contact forces are so strong that particles are easily prevented from following the background flow; thus, ordered structures cannot be developed. As long as the disordered structure is maintained under simple shear flows, the value of κ remains very close to that observed in extensional flows.

The shear-induced ordering can be hindered by mixing particles with different sizes. To see this effect, we consider two types of bidisperse suspensions with different size ratios: $a_2/a_1 = 1.2$ and $a_2/a_1 = 1.4$ (named ‘weak’ and ‘strong’ respectively). The two populations occupy the same volume fractions, i.e. $\phi_1 = \phi_2 = \phi/2$. In the weakly bidisperse suspensions (figure 3a), although the differences clearly become smaller, some flow-type dependence can still be seen, especially for $\phi = 0.5$. In the strongly bidisperse suspensions (figure 3b), we no longer see a noticeable flow-type dependence. Trouton ratios are always close to 4.

3.2. Pressure and anisotropic response

The total stress tensor σ is usually split into two parts: the isotropic pressure term and the traceless extra-stress term. Although only the extra-stress term determines the flows of incompressible fluids, the pressure p is also part of the material response. As seen in figure 4(a) for monodisperse suspensions in extensional flows, the pressure term p varies in a similar way to $\dot{\epsilon}\kappa$: the ratio $\dot{\epsilon}\kappa/p$ remains of the order of unity even when κ significantly increases by thickening. In our simulation, the volume

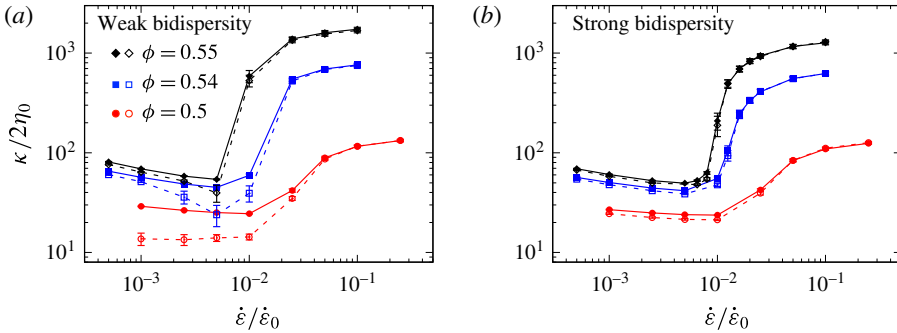


FIGURE 3. Mixing particles of different sizes hinders the shear-induced ordering. Differences in κ between extensional flow (filled symbols with solid lines) and simple shear (open symbols with dashed lines) are still present in the weakly bidisperse suspensions, $a_2/a_1 = 1.2$ (a), but no longer significant in the strongly bidisperse suspensions, $a_2/a_1 = 1.4$ (b).

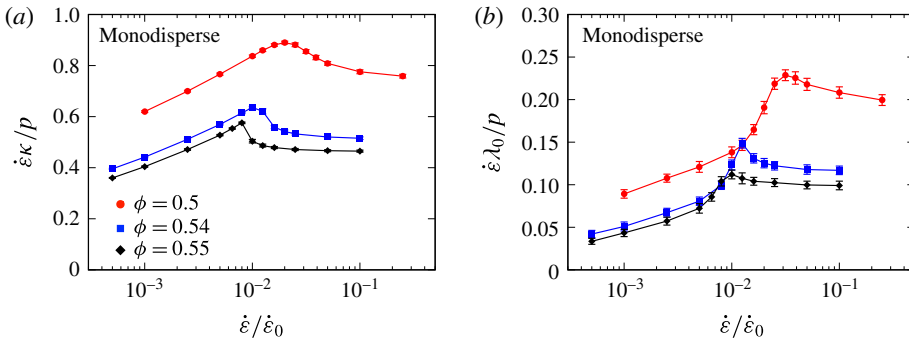


FIGURE 4. (a) The ratio between $\dot{\epsilon}\kappa$ and p for monodisperse suspensions in extensional flows remains of the order of unity even when the viscosity increases significantly. (b) The positive values of the ratio $\dot{\epsilon}\lambda_0/p$ for monodisperse suspensions in extensional flows indicate some anisotropy in the pressure response; that is, the in-plane pressure is higher than the out-of-plane pressure.

of the periodic cells is fixed; therefore, the system can never dilate. However, such increase of p with $\dot{\epsilon}\kappa$ suggests that extensional thickening (and shear thickening) of suspensions is a phenomenon related to that of dilatancy in granular materials.

The pressure term p contributes isotropically to σ by definition. However, there is another contribution to the stress σ sharing the same origin. The non-dissipative response associated with dilatancy can be anisotropic and activate the response function λ_0 . The dimensionless ratio $\dot{\epsilon}\lambda_0/p$ represents such anisotropy. Its positive values reported in figure 4(b) indicate that the in-plane pressure is higher than the out-of-plane pressure. However, this anisotropy is not very strong, as it would be if the pressure dilatancy were only present in the flow plane.

3.3. Reorientation angle of stress eigenvectors

Besides the ordering in simple shear flow, we can see some flow-type dependence in the reorientation angle φ , defined in (2.7). In extensional flows, the principal axes

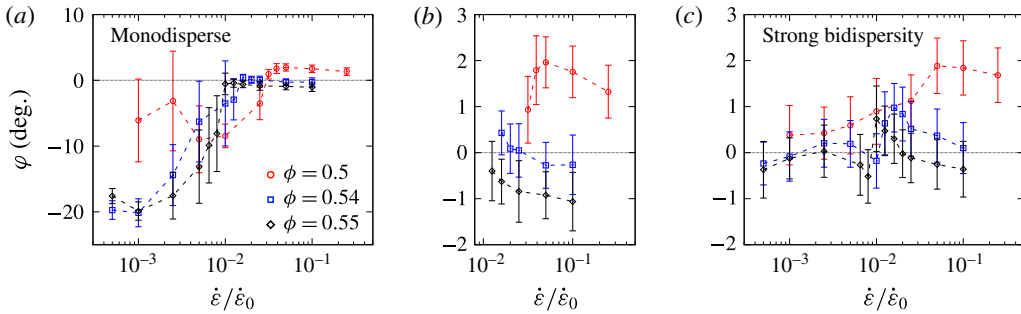


FIGURE 5. The reorientation angle φ is non-zero in simple shear flows for both monodisperse suspensions (a,b) and strongly bidisperse suspensions (c), while it fluctuates around zero in extensional flows (not shown). This angle is associated with the first normal stress difference N_1 , and we have $\varphi \approx -N_1/(4\dot{\epsilon}\kappa)$ when $\lambda_3 \ll \kappa$. The large standard deviations present in the monodisperse case (a) below thickening are due to the existence of several types of stable ordered structures displaying rather different values of φ . This is likely to be an effect originated by the finite size of the simulation cell. When the microstructure is disordered (b,c), the standard deviations are smaller and comparable.

of the stress tensor $\boldsymbol{\sigma}$ must be parallel to the eigenvectors of \mathbf{D} due to symmetry considerations. Indeed, the reorientation angle φ fluctuates around zero in those simulations. In simple shear flows, the shear-induced ordering is accompanied by large negative values of φ (figure 5a). On the other hand, in the disordered states above thickening (figure 5b) and with strong bidispersity (figure 5c), φ is always rather small but non-zero. In our inertialess simulation, this finite flow-type dependence indicates some characteristic microstructure (see § 3.4) due to the presence of vorticity in simple shear, which is absent in extensional flows.

It is worth commenting on the dependence of the angle φ on the volume fraction ϕ (figure 5). In the thickened regime, corresponding to higher values of $\dot{\epsilon}$, the angle φ is always positive for $\phi = 0.5$. The values of φ become smaller and can take slightly negative values as ϕ increases. This behaviour is consistent with some experimental measurements of N_1 , which is proportional to $-\lambda_3$. When the volume fraction is not very high, negative values have been observed for N_1 (Lee *et al.* 2006; Cwalina & Wagner 2014), corresponding to positive φ , while the sign of N_1 turns positive (negative φ) at higher volume fractions (Lootens *et al.* 2005; Dbouk *et al.* 2013).

3.4. Microstructure

As discussed in the modelling section § 2.2, it is reasonable to neglect particle and fluid inertia in the particle-scale dynamics. The response of such inertialess material elements to an imposed flow essentially depends on the microstructure built by the particles during the flow (Morris 2009). To measure the correlation of particle positions, we evaluate the pair distribution function $g(\mathbf{r}) \equiv P_{1|1}(\mathbf{r}|\mathbf{0})/n$, where n is the average number density of particles and $P_{1|1}(\mathbf{r}|\mathbf{0})$ is the conditional probability of finding a particle at \mathbf{r} with the condition that another particle is at the origin $\mathbf{0}$. Figure 6(a,b) shows $g(\mathbf{r})$ in the flow-plane slice $|z| < 0.1a$. We also consider angular distributions $g_c(\theta)$ for contacting (and nearly contacting) particles such that $|\mathbf{r}| < 2.02a$. The angle θ is measured from the $\hat{\mathbf{d}}_1$ axis.

As seen in figure 6(a), a stripe-patterned correlation $g(\mathbf{r})$ appears for the monodisperse suspensions in simple shear flow below thickening ($\dot{\epsilon}/\dot{\epsilon}_0 = 0.01$). The

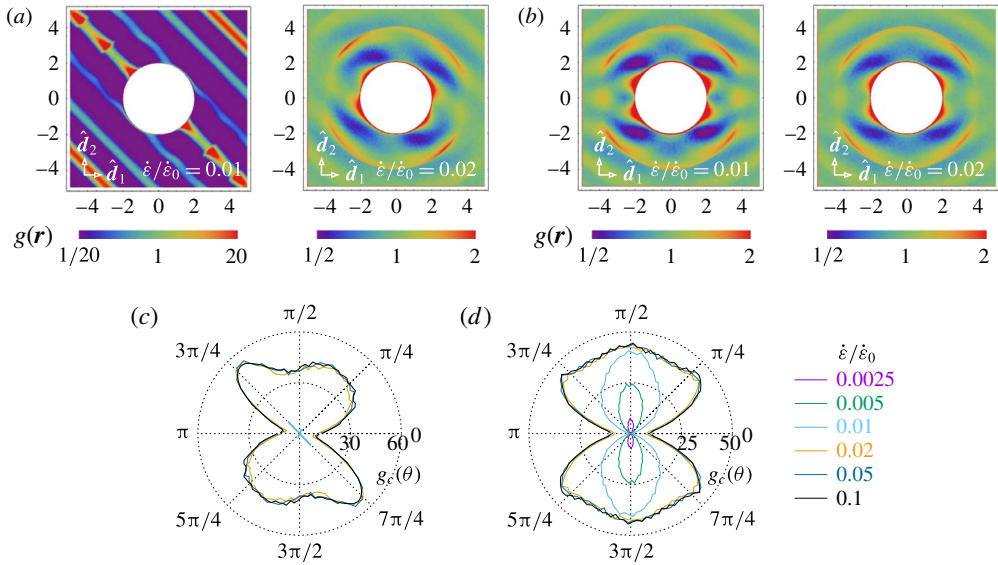


FIGURE 6. (a) The pair distribution function $g(\mathbf{r})$ highlights the presence of strong ordering below thickening ($\dot{\epsilon}/\dot{\epsilon}_0 = 0.01$) for monodisperse suspensions ($\phi = 0.54$) under simple shear, and its absence above thickening ($\dot{\epsilon}/\dot{\epsilon}_0 = 0.02$). (b) No obvious ordered structure can be associated with $g(\mathbf{r})$ for the case of extensional flow both below and above thickening. (c,d) The polar plot of the angular distribution $g_c(\theta)$ of contacting (and nearly contacting) particles such that $|\mathbf{r}| < 2.02a$ shows that the strong enhancement of contact interactions is mainly responsible for the thickening. It should be noted that, since practically no particles are in contact for $\dot{\epsilon}/\dot{\epsilon}_0 \leq 0.005$ in simple shear, the corresponding data in (c) are negligible. The difference between simple shear flow (c) and extensional flow (d) is discussed in the main text.

periodic peaks and striped correlation indicate the formation of chain-like structures by the particles. Once such chain-like structure is formed, particle interactions are rather weak, which leads to significantly low values of κ , as seen in figure 2. The microstructure is totally different above thickening ($\dot{\epsilon}/\dot{\epsilon}_0 = 0.02$). The long-range correlation is no longer seen. The correlation pattern indicates some disordered anisotropic microstructure. In figure 6(c), the angular contact distribution $g_c(\theta)$ clearly shows that the number of contacting particles increases remarkably for $\dot{\epsilon}/\dot{\epsilon}_0 \geq 0.02$. This observation is consistent with the idea that shear thickening is caused by the development of the contact network (Seto *et al.* 2013).

These results can be directly compared with those for the extensional flow simulation. As seen in figure 6(b), even below thickening ($\dot{\epsilon}/\dot{\epsilon}_0 = 0.01$), there is no long-range correlation in $g(\mathbf{r})$. The distribution pattern has horizontal and vertical mirror symmetries, and no vorticity skews the correlation in the extensional flow. The distribution pattern does not change much above thickening ($\dot{\epsilon}/\dot{\epsilon}_0 = 0.02$). However, a clear difference is present in the angular contact distribution $g_c(\theta)$ (figure 6d). A flame-shaped distribution transforms into a fan-shaped distribution at the extensional thickening transition. Thus, just below the transition, we can find contacting particles only around the directions of the compression axis. Nevertheless, the width of the flame shape indicates that, differently from what we observed under shear, the contact chains do not correspond to stable ordered chains of particles. Rather, they

are constantly rebuilt among new neighbouring particles. Such contact chains which are roughly parallel and oriented along the compression axis do not contribute to the viscosity significantly (figure 2). By contrast, above the thickening transition, contacting particles can be found in all directions, even in the directions of the extension axis ($\theta = 0$ and π). This distribution suggests an anisotropic network structure for the pattern of contacts, which enhances the viscosity. Thus, we can describe the essence of extensional thickening as a contact-chain to contact-network transition.

The fact that such a transition occurs in extensional flows without significant change of the long-range correlation (always absent) indicates that also in simple shear flows the contact-chain to contact-network transition is mainly responsible for the thickening. Indeed, while we observe a concurrent order–disorder structural transition in monodisperse suspensions under shear, this is not present in strongly bidisperse suspensions, which nevertheless display a strong thickening behaviour.

4. Conclusions

We numerically explored the non-Newtonian character of dense suspensions, which has a different origin from that of viscoelastic fluids. This character is manifested in three main aspects: rate dependence, non-dissipative responses and flow-type dependence. By analysing the thickening in both extensional and simple shear flows, we were able to confirm that the contact-chain to contact-network transition is its main cause. Non-dissipative responses, such as normal stress differences, are present in any flow regime. Flow-type dependence is evident in monodisperse suspensions below thickening, where ordering occurs under simple shear. The prevention of ordering through thickening or polydispersity hinders (but does not cancel) the flow-type dependence.

Acknowledgements

The authors acknowledge support from the Okinawa Institute of Science and Technology Graduate University. The research of R.S. is partially supported by JSPS KAKENHI Grant Number JP17K05618.

References

- AHAMADI, M. & HARLEN, O. G. 2008 A Lagrangian finite element method for simulation of a suspension under planar extensional flow. *J. Comput. Phys.* **227** (16), 7543–7560.
- BARNES, H. A. 1989 Shear-thickening ('dilatancy') in suspensions of nonaggregating solid particles dispersed in Newtonian liquids. *J. Rheol.* **33** (2), 329–366.
- BENDER, J. & WAGNER, N. J. 1996 Reversible shear thickening in monodisperse and bidisperse colloidal dispersions. *J. Rheol.* **40**, 899–916.
- BOSSIS, G. & BRADY, J. F. 1984 Dynamic simulation of sheared suspensions. I. General method. *J. Chem. Phys.* **80**, 5141–5154.
- BRADY, J. F. & BOSSIS, G. 1985 The rheology of concentrated suspensions of spheres in simple shear flow by numerical simulation. *J. Fluid Mech.* **155**, 105–129.
- BROWN, E. & JAEGER, H. M. 2009 Dynamic jamming point for shear thickening suspensions. *Phys. Rev. Lett.* **103**, 086001.
- CLAUD, C., BÉRUT, A., METZGER, B. & FORTERRE, Y. 2017 Revealing the frictional transition in shear-thickening suspensions. *Proc. Natl Acad. Sci. USA* **114** (20), 5147–5152.
- COUTURIER, É., BOYER, F., POULIQUEN, O. & GUAZZELLI, É. 2011 Suspensions in a tilted trough: second normal stress difference. *J. Fluid Mech.* **686**, 26–39.

- CWALINA, C. D. & WAGNER, N. J. 2014 Material properties of the shear-thickened state in concentrated near hard-sphere colloidal dispersions. *J. Rheol.* **58** (4), 949–967.
- DAI, S. & TANNER, R. I. 2017 Elongational flows of some non-colloidal suspensions. *Rheol. Acta* **56** (1), 63–71.
- DBOUK, T., LOBRY, L. & LEMAIRE, E. 2013 Normal stresses in concentrated non-Brownian suspensions. *J. Fluid Mech.* **715**, 239–272.
- FALL, A., HUANG, N., BERTRAND, F., OVARLEZ, G. & BONN, D. 2008 Shear thickening of cornstarch suspensions as a reentrant jamming transition. *Phys. Rev. Lett.* **100**, 018301.
- FERNANDEZ, N., MANI, R., RINALDI, D., KADAU, D., MOSQUET, M., LOMBOIS-BURGER, H., CAYER-BARRIOZ, J., HERRMANN, H. J., SPENCER, N. D. & ISA, L. 2013 Microscopic mechanism for shear thickening of non-Brownian suspensions. *Phys. Rev. Lett.* **111**, 108301.
- GIUSTERI, G. G. & SETO, R. 2017 A theoretical framework for steady-state rheometry in generic flow conditions. Preprint, [arXiv:1702.02745](https://arxiv.org/abs/1702.02745).
- GUY, B. M., HERMES, M. & POON, W. C. K. 2015 Towards a unified description of the rheology of hard-particle suspensions. *Phys. Rev. Lett.* **115**, 088304.
- HEUSSINGER, C. 2013 Shear thickening in granular suspensions: interparticle friction and dynamically correlated clusters. *Phys. Rev. E* **88**, 050201.
- HOFFMAN, R. L. 1998 Explanations for the cause of shear thickening in concentrated colloidal suspensions. *J. Rheol.* **42**, 111–123.
- KRAYNIK, A. M. & REINELT, D. A. 1992 Extensional motions of spatially periodic lattices. *Intl J. Multiphase Flow* **18** (6), 1045–1059.
- LAUN, H. M. 1984 Rheological properties of aqueous polymer dispersions. *Angew. Makromol. Chem.* **123** (1), 335–359.
- LAUN, H. M. 1994 Normal stresses in extremely shear thickening polymer dispersions. *J. Non-Newtonian Fluid Mech.* **54**, 87–108.
- LEE, M., ALCOUTLABI, M., MAGDA, J. J., DIBBLE, C., SOLOMON, M. J., SHI, X. & MCKENNA, G. B. 2006 The effect of the shear-thickening transition of model colloidal spheres on the sign of N_1 and on the radial pressure profile in torsional shear flows. *J. Rheol.* **50** (3), 293–311.
- LEES, A. W. & EDWARDS, S. F. 1972 The computer study of transport processes under extreme conditions. *J. Phys. C* **5** (15), 1921–1929.
- LIN, N. Y. C., GUY, B. M., HERMES, M., NESS, C., SUN, J., POON, W. C. K. & COHEN, I. 2015 Hydrodynamic and contact contributions to continuous shear thickening in colloidal suspensions. *Phys. Rev. Lett.* **115**, 228304.
- LOOTENS, D., VAN DAMME, H., HÉMAR, Y. & HÉBRAUD, P. 2005 Dilatant flow of concentrated suspensions of rough particles. *Phys. Rev. Lett.* **95**, 268302.
- MARI, R., SETO, R., MORRIS, J. F. & DENN, M. M. 2014 Shear thickening, frictionless and frictional rheologies in non-Brownian suspensions. *J. Rheol.* **58** (6), 1693–1724.
- MARI, R., SETO, R., MORRIS, J. F. & DENN, M. M. 2015a Discontinuous shear thickening in Brownian suspensions by dynamic simulation. *Proc. Natl Acad. Sci. USA* **112** (50), 15326–15330.
- MARI, R., SETO, R., MORRIS, J. F. & DENN, M. M. 2015b Nonmonotonic flow curves of shear thickening suspensions. *Phys. Rev. E* **91**, 052302.
- MELROSE, J. R. & BALL, R. C. 2004 ‘Contact networks’ in continuously shear thickening colloids. *J. Rheol.* **48**, 961–978.
- MILLER, R. M., SINGH, J. P. & MORRIS, J. F. 2009 Suspension flow modeling for general geometries. *Chem. Engng Sci.* **64** (22), 4597–4610.
- MORRIS, J. F. 2009 A review of microstructure in concentrated suspensions and its implications for rheology and bulk flow. *Rheol. Acta* **48**, 909–923.
- SAMI, S. 1996 Stokesian dynamics simulations of Brownian suspensions in extensional flow. MSc thesis, California Institute of Technology.
- SETO, R., MARI, R., MORRIS, J. F. & DENN, M. M. 2013 Discontinuous shear thickening of frictional hard-sphere suspensions. *Phys. Rev. Lett.* **111**, 218301.
- TANNER, R. I. & DAI, S. 2016 Particle roughness and rheology in noncolloidal suspensions. *J. Rheol.* **60** (4), 809–818.

Dense suspensions under extensional and shear flows

- TODD, B. D. & DAVIS, P. J. 1998 Nonequilibrium molecular dynamics simulations of planar elongational flow with spatially and temporally periodic boundary conditions. *Phys. Rev. Lett.* **81**, 1118–1121.
- WYART, M. & CATES, M. E. 2014 Discontinuous shear thickening without inertia in dense non-Brownian suspensions. *Phys. Rev. Lett.* **112**, 098302.
- ZINCHENKO, A. Z. & DAVIS, R. H. 2015 Extensional and shear flows, and general rheology of concentrated emulsions of deformable drops. *J. Fluid Mech.* **779**, 197–244.