

# From structure topology to chemical composition. XX. Titanium silicates: the crystal structure of hejmanite, $\text{Ba}_2\text{Mn}_4\text{Ti}_2(\text{Si}_2\text{O}_7)_2\text{O}_2(\text{OH})_2\text{F}_2$ , a Group-II TS-block mineral

E. SOKOLOVA<sup>1,\*</sup>, F. CÁMARA<sup>2,3</sup>, F. C. HAWTHORNE<sup>1</sup> AND L. A. PAUTOV<sup>4</sup>

<sup>1</sup> Department of Geological Sciences, University of Manitoba, Winnipeg, Manitoba R3T 2N2, Canada

<sup>2</sup> Dipartimento di Scienze della Terra, Università di Torino, I-10125, Torino, Italy

<sup>3</sup> CrisDi - Interdepartmental Center for Crystallography, via Giuria 7, 10126, Torino, Italy

<sup>4</sup> A.E. Fersman Mineralogical Museum, Russian Academy of Sciences, Leninskii Prospekt 18-2, Moscow 117071, Russia

[Received 27 May 2015; Accepted 28 August 2015; Associate Editor: Mark Welch]

## ABSTRACT

The crystal structure of hejmanite,  $\text{Ba}_2\text{Mn}_4\text{Ti}_2(\text{Si}_2\text{O}_7)_2\text{O}_2(\text{OH})_2\text{F}_2$ , from Mbolve Hill, Mkushi River area, Central Province, Zambia (holotype material) has been refined on a twinned crystal to  $R_1 = 1.88\%$  on the basis of 4539 [ $|F| > 4\sigma|F|$ ] reflections. Hejmanite is triclinic,  $C\bar{1}$ ,  $a = 10.716(2)$ ,  $b = 13.795(3)$ ,  $c = 11.778(2)$  Å,  $\alpha = 90.07(3)$ ,  $\beta = 112.24(3)$ ,  $\gamma = 90.03(3)$ °,  $V = 1612(2)$  Å<sup>3</sup>. Chemical analysis (electron microprobe) gives:  $\text{Ta}_2\text{O}_5$  0.09,  $\text{Nb}_2\text{O}_5$  1.27,  $\text{ZrO}_2$  0.65,  $\text{TiO}_2$  14.35,  $\text{SiO}_2$  23.13,  $\text{BaO}$  26.68,  $\text{SrO}$  0.19,  $\text{FeO}$  11.28,  $\text{MnO}$  15.12,  $\text{Cs}_2\text{O}$  0.05,  $\text{K}_2\text{O}$  0.33,  $\text{F}$  3.82,  $\text{H}_2\text{O}_{\text{calc}}$  1.63,  $\text{O} = \text{F} - 1.61$ , total 97.10 wt.%, where the  $\text{H}_2\text{O}$  content was calculated from the crystal-structure refinement, with  $(\text{OH} + \text{F}) = 4$  apfu. The empirical formula, calculated on the basis of 20 (O + F) anions, is of the form  $\text{A}_2^P\text{M}_4^{\text{O}}\text{M}_2^{\text{H}}(\text{Si}_2\text{O}_7)_2(\text{X}^{\text{O}})_4(\text{X}^{\text{P}})_2$ ,  $Z = 4$ :  $(\text{Ba}_{1.82}\text{K}_{0.07}\text{Sr}_{0.02})_{\Sigma 1.91}(\text{Mn}_{2.33}\text{Fe}_{1.65}^{2+}\text{Zr}_{0.04}\text{Mg}_{0.03})_{\Sigma 3.95}(\text{Ti}_{1.88}\text{Nb}_{0.10}\text{Zr}_{0.02})_{\Sigma 2}(\text{Si}_{2.02}\text{O}_7)_2\text{O}_2[(\text{OH})_{1.89}\text{F}_{0.11}]_{\Sigma 2}\text{F}_2$ . The crystal structure is a combination of a TS (Titanium Silicate) block and an I (intermediate) block. The TS block consists of HOH sheets (H – heteropolyhedral, O – octahedral). The topology of the TS block is as in Group-II TS-block minerals: Ti (+ Nb) = 2 apfu per  $(\text{Si}_2\text{O}_7)_2$  [as defined by Sokolova (2006)]. In the O sheet, five  $^{[6]}M^{\text{O}}$  sites are occupied mainly by Mn, less Fe<sup>2+</sup> and minor Zr and Mg, with  $\langle M^{\text{O}}-\varphi \rangle = 2.198$  Å ( $\varphi = \text{O}, \text{OH}$ ), ideally giving  $\text{Mn}_4$  apfu. In the H sheet, two  $^{[6]}M^{\text{H}}$  sites are occupied mainly by Ti, with  $\langle M^{\text{H}}-\varphi \rangle = 1.962$  Å ( $\varphi = \text{O}, \text{F}$ ), ideally giving  $\text{Ti}_2$  apfu; four  $^{[4]}S_i$  sites are occupied by Si, with  $\langle \text{Si}-\text{O} \rangle = 1.625$  Å. The  $M^{\text{H}}$  octahedra and  $\text{Si}_2\text{O}_7$  groups constitute the H sheet. The two  $^{[12]}B_a$ -dominant  $A^P(1,2)$  sites, with  $\langle A^P-\varphi \rangle = 2.984$  Å ( $\varphi = \text{O}, \text{F}$ ), ideally give  $\text{Ba}_2$  apfu. Two  $X_M^{\text{O}}(1,2)$  and two  $X_A^{\text{O}}(1,2)$  sites are occupied by O atoms and OH groups with minor F, respectively, ideally giving  $(\text{X}^{\text{O}})_4 = (\text{X}_M^{\text{O}})_2 + (\text{X}_A^{\text{O}})_2 = \text{O}_2(\text{OH})_2$  pfu. Two  $X_M^P(1,2)$  sites are occupied by F, giving  $\text{F}_2$  apfu. TS blocks link via a layer of Ba atoms which constitute the I block. Simplified and end-member formulae of hejmanite are  $\text{Ba}_2(\text{Mn}, \text{Fe}^{2+})_4\text{Ti}_2(\text{Si}_2\text{O}_7)_2\text{O}_2(\text{OH}, \text{F})_2\text{F}_2$  and  $\text{Ba}_2\text{Mn}_4\text{Ti}_2(\text{Si}_2\text{O}_7)_2\text{O}_2(\text{OH})_2\text{F}_2$ ,  $Z = 4$ . Hejmanite is a Mn-analogue of bafertisite,  $\text{Ba}_2\text{Fe}_2^{2+}\text{Ti}_2(\text{Si}_2\text{O}_7)_2\text{O}_2(\text{OH})_2\text{F}_2$ .

**KEYWORDS:** hejmanite, holotype, electron microprobe, single-crystal X-ray diffraction, crystal structure, chemical formula, TS block, Group II.

## Introduction

SEMENOV and Zhang Peishan (1959) described bafertisite,  $\text{BaFe}_2\text{TiSi}_2\text{O}_9$ ,  $Z = 2$ , as a new mineral from the Bayan Obo rare-earth element (REE) deposit, Inner Mongolia, China. The crystal

\*E-mail: elena\_sokolova@umanitoba.ca  
DOI: 10.1180/minmag.2016.080.026

structure of bafertisite from the Bayan Obo deposit was determined by (1) Guan *et al.* (1963) and (2) Peng Zhizhong and Shen Jinchuan (1963): [1] monoclinic, space group  $Cm$ ,  $a = 10.60$ ,  $b = 13.64$ ,  $c = 12.47$  Å,  $\beta = 119.5^\circ$ , [2] monoclinic, space group  $P2_1/m$ ,  $a = 10.98$ ,  $b = 6.80$ ,  $c = 5.36$  Å,  $\beta = 94^\circ$ . Based on the structure-refinement results, Guan *et al.* (1963) and Peng Zhizhong and Shen Jinchuan (1963) gave the chemical formula of bafertisite as follows:  $BaFe_2Ti[Si_2O_7]O(OH)_2$ ,  $Z = 8$  and 2, respectively. Vrána *et al.* (1992) described hejtmánnite from Mbolve Hill, Mkushi River area, Central Province, Zambia, as a manganese-dominant analogue of bafertisite: monoclinic, diffraction symbol  $C^{*/\#}$ ,  $a = 10.698(4)$ ,  $b = 13.768(5)$ ,  $c = 11.748(4)$  Å,  $\beta = 112.27(2)^\circ$ ,  $V = 1601(2)$  Å<sup>3</sup>,  $D_{\text{meas.}} = 4.02$  g/cm<sup>3</sup>. Vrána *et al.* (1992) determined the chemical composition of hejtmánnite by electron microprobe (Table 2) and by analogy with bafertisite (Semenov and Zhang Peishan, 1959; Guan *et al.*, 1963; Peng Zhizhong and Shen Jinchuan, 1963), gave simplified and endmember formulae  $Ba(Mn,Fe)_2TiO(Si_2O_7)(OH, F)_2$  and  $BaMn_2TiO(Si_2O_7)(OH,F)_2$ ,  $Z = 8$ . Pautov (pers comm., 1989; in Minerals. Handbook. Silicates, 1996) reported the occurrence of a Mn-analogue of bafertisite in a rhodonite-tephroite-spessartine-quartz association from the Muzeinoe gorge, the Inyl'chek mountain ridge, Tyan-Shan, South-Eastern Kirgizia, and gave its empirical and general formulae,  $(Ba_{0.96}Na_{0.03}Ca_{0.01}Cs_{0.002})_{\Sigma 1}(Mn_{1.70}Fe^{2+}_{0.17}Mg_{0.05}Al_{0.08})_{\Sigma 2}(Ti_{0.93}Sn_{0.07}Nb_{0.015})_{\Sigma 1.01}(Si_{1.97}Al_{0.02})_{\Sigma 1.99}O_7O_{2.09}(H_2O)_{0.25}$  and  $BaMn_2TiO(Si_2O_7)(OH)_2$ , respectively. All the crystals of the material from Inyl'chek were extensively twinned, and complicated the structure work. Sokolova *et al.* (1989) reported the unit cell for the Mn-analogue of bafertisite from the Inyl'chek mountain ridge,  $BaMn_2TiO(Si_2O_7)(OH)_2$ ; triclinic, space groups  $P\bar{1}$  or  $P\bar{1}$ ,  $a = 10.767(7)$ ,  $b = 13.858(9)$ ,  $c = 32.99(6)$  Å,  $\alpha = 90.3(1)$ ,  $\beta = 94.6(1)$ ,  $\gamma = 89.96(5)^\circ$ ,  $V = 4906(2)$  Å<sup>3</sup>,  $Z = 24$ , and the structure model for the monoclinic subcell: space group  $Pm$ ,  $a = 5.374(3)$ ,  $b = 6.911(3)$ ,  $c = 32.82(1)$  Å,  $\beta = 94.62(4)^\circ$ ,  $V = 1214(2)$  Å<sup>3</sup>,  $R = 19.89\%$ . They showed that the general topology of the structure of the Mn-analogue of bafertisite from the Inyl'chek mountain ridge is identical to that of bafertisite (Guan *et al.*, 1963). Rastsvetaeva *et al.* (1991) collected new X-ray diffraction data using the crystal of the Mn-analogue of bafertisite from the Inyl'chek mountain ridge previously studied by Sokolova *et al.* (1989). They considered the crystal in question to be an intergrowth of two monoclinic phases of the

composition  $BaMn_2TiO(Si_2O_7)(OH)_2$ : (1) space group  $P2_1/m$ ,  $a = 5.361$ ,  $b = 6.908$ ,  $c = 12.556$  Å,  $\beta = 119.8^\circ$ ,  $V = 403$  Å<sup>3</sup>,  $Z = 2$ ,  $R = 6.8\%$ ; and (2) space group  $Cm$ ,  $a = 10.723$ ,  $b = 13.812$ ,  $c = 12.563$  Å,  $\beta = 119.9^\circ$ ,  $V = 1613$  Å<sup>3</sup>,  $Z = 8$ ,  $R = 8.3\%$ ; both phases are isostructural with bafertisite [*cf.*  $P2_1/m$  and  $Cm$  bafertisite structures of Peng Zhizhong and Shen Jinchuan (1963) and Guan *et al.* (1963), respectively]. However, both structures of Rastsvetaeva *et al.* (1991) have Si–O distances that are too short: (1) space group  $P2_1/m$ : 1.54 Å; and (2) space group  $Cm$ : 1.49 Å. These distances imply significant errors in both structures. The problems with the crystal structure of hejtmánnite arise from the poor quality of its crystals, which is related to the extensive twinning [*cf.* bafertisite, Cámará *et al.* (2015b)] and possible intergrowths with other phases, a common problem with TS-block minerals. Based on the structure work of Rastsvetaeva *et al.* (1991), Sokolova (2006) and Sokolova and Cámará (2013) considered hejtmánnite a TS-block mineral with two modifications: hejtmánnite-C (space group  $Cm$ ) and hejtmánnite-P (space group  $P2_1/m$ ).

The TS (Titanium Silicate) block is the main structural unit in the fast-growing family of 40 minerals: 34 minerals are listed in Sokolova and Cámará (2013), and information on six minerals, kolskyite, emmerichite, saamite, betalomonosovite, bobshannonite and fogoite-(Y) can be found in Cámará *et al.* (2013), Akseenov *et al.* (2014), Cámará *et al.* (2014a), Sokolova *et al.* (2015a,b) and Cámará *et al.* (2015a), respectively [*cf.* 24 minerals (Sokolova, 2006)]. The TS block consists of a central trioctahedral (O) sheet and two adjacent heteropolyhedral (H) sheets of [5–7]-coordinated polyhedra and  $Si_2O_7$  groups. The TS block is characterized by a planar cell based on minimal lengths of translational vectors,  $t_1 \approx 5.5$  and  $t_2 \approx 7$  Å, and  $t_1 \wedge t_2 \approx 90^\circ$ . The general formula of the TS block is  $A_2^P B_2^P M_2^H M_4^O (Si_2O_7)_2 X_{4+n}$ , where  $M_2^H$  and  $M_4^O$  = cations of the H and O sheets;  $M^H = Ti$ ,  $Nb$ ,  $Zr$ ,  $Y$ ,  $Mn$ ,  $Ca + REE$ ,  $Ca$ ;  $M^O = Ti$ ,  $Zr$ ,  $Nb$ ,  $Fe^{2+}$ ,  $Fe^{3+}$ ,  $Mg$ ,  $Mn$ ,  $Ca$ ,  $Na$ ;  $A^P$  and  $B^P$  = cations at the peripheral ( $P$ ) sites =  $Na$ ,  $Ca + REE$ ,  $Ca$ ,  $Ba$ ,  $Sr$ ,  $K$ ;  $X$  = anions,  $O$ ,  $OH$ ,  $F$  and  $H_2O$  groups;  $X_{4+n} = X_4^O + X_n^P$ ,  $n = 0, 1, 1.5, 2, 4$ , where  $X_4^O$  = anions of the O sheet which do not coordinate Si atoms,  $X_n^P$  = anions at the periphery of the TS block;  $X = O$ ,  $OH$ ,  $F$ ,  $H_2O$  (Sokolova and Cámará, 2013). Sokolova (2006) developed general structural principles for the TS-block minerals. There are three topologically distinct TS blocks based on three types of linkage of H and O sheets. In the crystal structures of TS-block minerals, TS blocks either link directly

or alternate with intermediate (**I**) blocks. The **I** block consists of alkali and alkaline-earth cations, oxyanions ( $\text{PO}_4$ ), ( $\text{SO}_4$ ) and ( $\text{CO}_3$ ) and  $\text{H}_2\text{O}$  groups. Sokolova (2006) divided TS-block structures into four Groups, based on the topology and stereochemistry of the TS block. Each group of structures has a different linkage, content and stereochemistry of Ti (+ Nb + Zr +  $\text{Fe}^{3+}$  + Mg + Mn) per  $(\text{Si}_2\text{O}_7)_2$ . In Group I, Ti (+ Nb + Zr) = 1 atom per formula unit (apfu); in Group II, Ti (+ Nb) = 2 apfu; in Group III, Ti (+ Nb + Mg +  $\text{Fe}^{3+}$ ) = 3 apfu; in Group IV, Ti (+ Mg + Mn) = 4 apfu. In a TS-block structure, four types of self-linkage between adjacent TS blocks occur.

Sokolova and Cámará (2013) introduced the concept of ‘basic’ and ‘derivative structures’ for TS-block minerals. A basic structure has the following four characteristics: (1) there is only one type of TS block; (2) the two H sheets of the TS block are identical; (3) there is only one type of **I** block or it is absent; (4) there is only one type of self-linkage of TS blocks. Basic structures obey the general structural principles laid out by Sokolova (2006). A derivative structure has one or more of the three following characteristics: (1) there is more than one type of TS block; (2) there is more than one type of **I** block; (3) there is more than one type of self-linkage of TS blocks. A derivative structure is related to two or more basic structures of the same Group: it can be derived by adding these structures via sharing the central O sheet of the TS blocks of adjacent structural fragments which represent basic structures. There are 35 basic TS-block structures and five derivative TS-block structures.

Following our continued interest in TS-block minerals, we felt strongly that the crystal structure of hejtmanite must be solved and refined on the holotype material of Vrána *et al.* (1992). We studied hejtmanite from: (1) Mbolve Hill, Mkushi River area, Central Province, Zambia (holotype material from the collection of Leonid A. Pautov, given to Leonid by Stanislav Vrána); and (2) from the Muzeinoe gorge, the Inyl'chek mountain ridge, Tyan-Shan, South-Eastern Kirgizia. The current paper reports the crystal structure and structural formula of hejtmanite,  $\text{Ba}_2\text{Mn}_4\text{Ti}_2(\text{Si}_2\text{O}_7)_2\text{O}_2(\text{OH})_2\text{F}_2$ , a TS-block mineral of Group II where Ti (+ Nb) = 2 apfu per  $(\text{Si}_2\text{O}_7)_2$  (Table 1).

## Chemical composition

Crystals of hejtmanite were analysed with a Cameca SX-100 electron microprobe operating in

wavelength-dispersive mode with an accelerating voltage of 15 kV, a specimen current of 10 nA and a beam diameter of 10  $\mu\text{m}$ . The following standards were used: Si: diopside; Ta:  $\text{Mn}(\text{Ta}_{1.70}\text{Nb}_{0.30})\text{O}_6$ ; Nb, Ba:  $\text{Ba}_2\text{NaNb}_5\text{O}_{15}$ ; Zr: zircon; Ti: titanite; Fe: fayalite; Mn: spessartine; Mg: forsterite; Sn: cassiterite; Sr:  $\text{SrTiO}_3$ ; Cs: pollucite; K: orthoclase; F: fluorite. The elements Na, Al, Zn, Ca, Pb, Rb and Cl were sought but not detected. The data were reduced and corrected by the *PAP* method of Pouchou and Pichoir (1985). The  $\text{H}_2\text{O}$  (presence of OH groups confirmed by IR spectroscopy, Vrána *et al.*, 1992) was calculated from the results of the crystal-structure analysis on the basis that  $\text{F} + \text{OH} = 4$  apfu. Table 2 gives the chemical composition of hejtmanite from Zambia (holotype material) compared with its original chemical analysis (Vrána *et al.*, 1992) and hejtmanite from Inyl'chek, Kirgizia. The empirical formula was calculated on the basis of 20 (O + F) anions and is of the form  $\text{A}_2^P\text{M}_4^{\text{O}}\text{M}_2^{\text{H}}(\text{Si}_2\text{O}_7)_2(\text{X}^{\text{O}})_4(\text{X}^{\text{P}})_2$ ,  $Z = 4$ . For hejtmanite from Zambia (holotype), it is  $(\text{Ba}_{1.82}\text{K}_{0.07}\text{Sr}_{0.02})_{\Sigma 1.91}(\text{Mn}_{2.33}\text{Fe}_{2.15}^{2+}\text{Zr}_{0.04}\text{Mg}_{0.03})_{\Sigma 3.95}(\text{Ti}_{1.88}\text{Nb}_{0.10}\text{Zr}_{0.02})_{\Sigma 2}(\text{Si}_{2.02}\text{O}_7)_2\text{O}_2[(\text{OH})_{1.89}\text{F}_{0.11}]_{\Sigma 2}\text{F}_2$ ,  $D_{\text{calc.}} = 4.189 \text{ g/cm}^3$  and is in accord with  $D_{\text{meas.}} = 4.02 \text{ g/cm}^3$  (Vrána *et al.*, 1992). For hejtmanite from Inyl'chek, Kirgizia, it is  $\text{Ba}_{1.92}(\text{Mn}_{3.62}\text{Fe}_{2.25}^{2+}\text{Mg}_{0.08}\text{Zr}_{0.02})_{\Sigma 3.97}(\text{Ti}_{1.59}\text{Sn}_{0.42})_{\Sigma 2.01}(\text{Si}_{2.02}\text{O}_7)_2\text{O}_2[(\text{OH})_{1.93}\text{F}_{0.07}]_{\Sigma 2}\text{F}_2$ ,  $D_{\text{calc.}} = 4.189 \text{ g/cm}^3$ . Hejtmanite from Inyl'chek, Kirgizia, is characterized by very high MnO, significant SnO<sub>2</sub>, lower TiO<sub>2</sub> and lack of Nb<sub>2</sub>O<sub>5</sub>: 23.91, 5.95, 11.82 and 0 wt.%, respectively, cf. 14.12, 0, 14.35 and 1.27 wt.%, respectively (hejtmanite from Zambia, this work) (Table 2). By analogy with Sn-rich astrophyllite where Sn<sup>4+</sup> constitutes ~31% of the Ti-dominant D site in the H sheet of the HOH block (Cámará *et al.*, 2010), we assigned all Sn<sup>4+</sup> to the Ti-dominant M<sup>H</sup> site in the H sheet of the TS block (Table 2):  $(\text{Ti}_{1.59}\text{Sn}_{0.42})_{\Sigma 2.01}$  apfu. Simplified and end-member formulae of hejtmanite are  $\text{Ba}_2(\text{Mn}, \text{Fe}^{2+})_4\text{Ti}_2(\text{Si}_2\text{O}_7)_2\text{O}_2(\text{OH}, \text{F})_2\text{F}_2$  and  $\text{Ba}_2\text{Mn}_4\text{Ti}_2(\text{Si}_2\text{O}_7)_2\text{O}_2(\text{OH})_2\text{F}_2$ ,  $Z = 4$ .

## Crystal structure

### Data collection and structure refinement

Single-crystal X-ray data for hejtmanite from Zambia were collected using a Bruker APEX II ULTRA three-circle diffractometer with a rotating-anode generator ( $\text{MoK}\alpha$ ), multilayer optics and an APEX II 4 K CCD detector. The intensities of 4539 [ $|F| > 4\sigma |F|$ ] reflections with  $-15 < h < 15$ ,

TABLE 1. Ideal structural formulae\* and unit-cell parameters for Group-II TS-block minerals, Ti + Nb = 2 apfu per  $(\text{Si}_2\text{O}_7)_2$ .

Mineral Structure type**	Formula						$a$ (Å)	$b$ (Å)	$c$ (Å)	Sp. gr.	$Z$	Ref.		
	$\text{A}_{1-2}^P$	$\text{B}_{0-2}^P$	$\text{M}_4^{\text{O}}$	$\text{M}_2^{\text{H}}$	$(\text{Si}_2\text{O}_7)_2$	$\text{O}_2$	$(\text{OH})_2$	$\text{F}_2$	$90.07$	$112.24$	$90.03$	$\bar{C}\bar{I}$	$4$ (1)	
hejmanite B2(GII)	Ba <sub>2</sub>	Mn <sub>4</sub>	Ti <sub>2</sub>	(Si <sub>2</sub> O <sub>7</sub> ) <sub>2</sub>	O <sub>2</sub>	(OH) <sub>2</sub>	F <sub>2</sub>	10.716	13.795	11.778	C $\bar{I}$	4		
baertsite B2(GII) <sup>1</sup>	Ba <sub>2</sub>	Fe <sub>2+</sub> <sup>+</sup>	Ti <sub>2</sub>	(Si <sub>2</sub> O <sub>7</sub> ) <sub>2</sub>	O <sub>2</sub>	(OH) <sub>2</sub>	F <sub>2</sub>	10.677	13.767	11.737	C $\bar{I}$	4		
cámaraita <sup>1</sup> D1(GII)	Ba <sub>3</sub>	Na	Fe <sub>8</sub> <sup>2+</sup>	Ti <sub>4</sub>	(Si <sub>2</sub> O <sub>7</sub> ) <sub>4</sub>	O <sub>4</sub>	(OH) <sub>4</sub>	F <sub>3</sub>	10.6965	13.7861	21.478	C $\bar{I}$	4	
jinshjiangite B1(GII)	Ba	Na	Fe <sub>4</sub> <sup>2+</sup>	Ti <sub>2</sub>	(Si <sub>2</sub> O <sub>7</sub> ) <sub>2</sub>	O <sub>2</sub>	(OH) <sub>2</sub>	F	10.7059	13.7992	20.760	C $\bar{I}$	8	
peraultite B1(GII)	Ba	Na	Mn <sub>4</sub>	Ti <sub>2</sub>	(Si <sub>2</sub> O <sub>7</sub> ) <sub>2</sub>	O <sub>2</sub>	(OH) <sub>2</sub>	F	90.008	94.972	89.984	C2	8	
bobshannonite <sup>1</sup> B1(GII)	Ba K	Na <sub>2</sub>	(Mn,Na) <sub>8</sub>	(Nb,Ti) <sub>4</sub>	(Si <sub>2</sub> O <sub>7</sub> ) <sub>4</sub>	O <sub>4</sub>	(OH) <sub>4</sub>	(O,F) <sub>2</sub>	10.731	13.841	20.845	C2	8	
yoshimurite <sup>2</sup> B3(GII)	Ba <sub>2</sub>	Ba <sub>2</sub>	Mn <sub>4</sub>	[Si]Ti <sub>2</sub>	(Si <sub>2</sub> O <sub>7</sub> ) <sub>2</sub>	(PO <sub>4</sub> ) <sub>2</sub>	O <sub>2</sub>	(OH) <sub>2</sub>	90	95.06	90	C $\bar{I}$	4	
bussenite <sup>3</sup> B4(GII)	(Na□) <sub>2</sub>	Ba <sub>2</sub>	(M <sup>2+</sup> Na) <sub>2</sub>	Ti <sub>2</sub>	(Si <sub>2</sub> O <sub>7</sub> ) <sub>2</sub>	(CO <sub>3</sub> ) <sub>2</sub>	O <sub>2</sub>	(H <sub>2</sub> O) <sub>2</sub>	F <sub>2</sub>	10.839	13.912	20.98	P $\bar{I}$	2
										89.99	95.02	89.998		
										5.386	6.999	14.748		
										95.50	93.62	89.98		
										5.399	7.016	16.254		
										102.44	93.18	90.10		

\*The general structural formula of the TS block is  $\text{A}_2^P \text{B}_2^P \text{M}_2^{\text{O}} \text{M}_2^{\text{H}} (\text{Si}_2\text{O}_7)_2 \text{X}_{4-n}$ , where  $\text{M}_2^{\text{H}}$  and  $\text{M}_2^{\text{O}}$  = cations of the H and O sheets;  $\text{A}'$  and  $\text{B}'$  = cations at the peripheral ( $P$ ) sites; X = anions;  $\text{X}_{4-n} = \text{X}_4^{\text{O}} + \text{X}_{4-n}^{\text{P}}$ ,  $n = 0, 1, 1.5, 2, 4$  (Sokolova and Cámarita, 2013).  $\text{X}_4^{\text{O}} = (\text{XM})_2 + (\text{XA})_2$ ;  $\text{X}_M^{\text{O}} =$  anions at common vertices of  $3\text{M}^{\text{O}}$  and  $\text{M}^{\text{H}}$  polyhedra and  $\text{X}_A^{\text{O}}$  = anions at common vertices of  $3\text{M}^{\text{O}}$  and  $\text{A}'^{\text{P}}$  polyhedra (where  $\text{A}'^{\text{P}} - \text{X}_A^{\text{O}} < 3$  Å);  $\text{X}_M^{\text{P}}$  = apical anions of  $\text{M}^{\text{H}}$  cations at the periphery of the TS block. The stoichiometry of the core part of the TS block,  $\text{M}_2^{\text{O}} \text{M}_2^{\text{H}} (\text{Si}_2\text{O}_7)_2 \text{X}_4^{\text{O}}$ , is invariant in all structures (shown in bold). In Group II,  $\text{A}'^{\text{P}}$  and  $\text{B}'^{\text{P}}$  cations, plus  $(\text{PO}_4)_2$  (in yoshimurite) and  $(\text{Na□})_2(\text{CO}_3)_2 \text{F}_2$  (in bussenite) constitute the I block.

\*\*Ba(GII) and Dn(GII) denote B for basic and D for derivative structures of Group II (Sokolova and Cámarita, 2013). For yoshimurite and bussenite, ideal structural formulae are from Sokolova (2006). Surkhobite (Rastsvetaeva *et al.*, 2008) is not listed here as there are problems with its crystal structure.

<sup>1</sup>The formulae for cámaraita and bobshannonite are per double minimal cell based on  $2t_1$  and  $2t_2$  translations  $[(\text{Si}_2\text{O}_7)_4]$ .

<sup>2</sup>There are misprints in McDonald *et al.* (2000):  $\alpha = 89.98$ ,  $\gamma = 95.50^\circ$ ;

<sup>3</sup> $\text{M}^{2+} = \text{Fe}^{2+}$ , Mn;

References (the most recent reference on the structure): (1) this work; (2) Cámarita *et al.* (2015b); (3) Cámarita *et al.* (2009); (4) Cámarita *et al.* (2016); (5) Yannova *et al.* (1998); (6) Sokolova *et al.* (2015b); (7) McDonald *et al.* (2000); (8) Zhou *et al.* (2002).

## THE CRYSTAL STRUCTURE OF HEJTMANITE

TABLE 2. Chemical composition and unit formula\* for hejtmomite.

Component	wt.%			Formula unit (apfu)		
	Zambia (holotype)		Inyl'chek, Kirgizia	Zambia (holotype)	Inyl'chek, Kirgizia	
	This work	Vrána <i>et al.</i> (1992)	This work	This work	Vrána <i>et al.</i> (1992)	This work
Ta <sub>2</sub> O <sub>5</sub>	0.09	n.d.	n.d.	Si	4.04	4.11
Nb <sub>2</sub> O <sub>5</sub>	1.27	1.4	n.d.			
SnO <sub>2</sub>	n.d.	n.d.	5.95	Mn	2.23	2.09
ZrO <sub>2</sub>	0.65	n.d.	0.22	Fe <sup>2+</sup>	1.65	1.65
TiO <sub>2</sub>	14.35	13.27	11.82	Zr	0.04	0
SiO <sub>2</sub>	23.13	23.52	22.53	Mg	0.03	0.03
Al <sub>2</sub> O <sub>3</sub>	n.d.	0.37	n.d.	Na	0	0.02
BaO	26.68	30.20	27.41	$\Sigma 4M^O$	3.95	3.79
SrO	0.19	n.d.	n.d.			
FeO	11.28	11.29	1.65	Ti	1.88	1.75
MnO	15.12	14.12	23.91	Sn	0	0
CaO	n.d.	n.d.	0.04	Nb	0.10	0.11
MgO	0.12	0.13	0.30	Zr	0.02	0
Cs <sub>2</sub> O	0.05	n.d.	0.04	Al	0	0.08
K <sub>2</sub> O	0.33	0.30	n.d.	$\Sigma 2M^H$	2.00	1.94
Na <sub>2</sub> O	n.d.	0.06	n.d.			
H <sub>2</sub> O**	1.63	1.86	1.62	Ba	1.82	2.07
F	3.82	3.30	3.66	Sr	0.02	0
Cl	n.d.	<0.1	n.d.	K	0.07	0.07
-O=F <sub>2</sub> ,Cl <sub>2</sub>	1.61	1.39	1.54	$\Sigma 2A^P$	1.91	2.14
Total	97.10	98.43	97.61			
				$\Sigma$ cations	11.90	11.98
				F	2.11	1.82
				OH	1.89	2.18
				$\Sigma 2X_M^P + 2X_A^O$	4.00	4.00

n.d. – not detected.

\*Calculated on anion basis: O + F = 20 apfu.

\*\*Calculated from structure solution and refinement (this work) and by crystallochemical calculations (Vrána *et al.*, 1992): OH + F = 4 apfu.

$-19 < k < 19$ ,  $-16 < l < 16$  were measured to 60.28° 20 using 16 s per 0.3° frame. Unit-cell dimensions were determined by least-squares refinement of 9989 reflections with  $I > 10\sigma I$ , and are given in Table 3, together with other miscellaneous information on data collection and structure refinement. An absorption correction was undertaken using the SADABS program (Sheldrick, 2008). The unit-cell dimensions of hejtmomite (this work) are in good agreement with those of Vrána *et al.* (1992) (Table 3). All calculations were carried out with the Bruker SHELXTL version 5.1 system of programs (Sheldrick, 2008). The crystal structure was refined in space group  $C\bar{1}$  using the atom coordinates of bafertisite (*Cámará et al.*, 2015b) and

refined to  $R_1 = 1.88\%$  on a twinned crystal with two components related by the twin matrix [100 010 001] and a twin ratio of 0.526(1):0.474(1). The (Niggli) reduced unit cell is:  $a = 8.732(2)$ ,  $b = 8.736(2)$ ,  $c = 11.778(2)$  Å,  $\alpha = 103.37(3)$ ,  $\beta = 103.48(3)$ ,  $\gamma = 104.32(3)$ °,  $V = 806(1)$  Å<sup>3</sup>,  $P\bar{1}$ ,  $Z = 2$ . The  $P\bar{1}$  unit cell can be derived from the  $C\bar{1}$  unit cell via the transformation matrix [ $\frac{1}{2} \frac{1}{2} 0 \frac{1}{2} \frac{1}{2} 0 001$ ]. We chose the unconventional space group  $C\bar{1}$  for consistency of orientation with all other thirty-nine TS-block structures characterized by the planar cell based on minimal lengths of translational vectors,  $t_1 \approx 5.5$  and  $t_2 \approx 7$  Å, and  $t_1 \approx t_2 \approx 90^\circ$ , and specifically with bafertisite, the Fe<sup>2+</sup>-analogue of hejtmomite. Scattering curves for neutral atoms were taken from

TABLE 3. Miscellaneous refinement data for hejtmanite.

	This work	Vrána <i>et al.</i> (1992)
<i>a</i> (Å)	10.716(2)	10.698(4)
<i>b</i>	13.795(3)	13.768(5)
<i>c</i>	11.778(2)	11.748(4)
$\alpha$ (°)	90.07(3)	90
$\beta$	112.24(3)	112.27(2)
$\gamma$	90.03(3)	90
<i>V</i> (Å <sup>3</sup> )	1612(2)	1601(2)
Space group	<i>C</i> 1	<i>C</i> */*
<i>Z</i>	4	4
Absorption coefficient (mm <sup>-1</sup> )	9.00	
<i>F</i> (000)	1885.8	
<i>D</i> <sub>calc.</sub> (g/cm <sup>3</sup> )	4.189	4.29
Crystal size (mm)	0.004 × 0.025 × 0.040	
Second component*	0.474(1)	
Radiation/monochromator	MoK $\alpha$ /graphite	
2θ range for data collection (°)	60.28	
<i>R</i> (int) (%)	1.32	
Reflections collected	9468	
Independent reflections		
<i>F</i> <sub>o</sub> > 4σ <i>F</i>	4539	4748
Refinement method	Full-matrix least squares on <i>F</i> <sup>2</sup> , fixed weights proportional to 1/σ <i>F</i> <sub>o</sub> <sup>2</sup>	
No. of refined parameters	308	
Final <i>R</i> indices (%)		
<i>R</i> <sub>1</sub> ( <i>F</i> <sub>o</sub> > 4σ <i>F</i> )	1.88	
<i>R</i> <sub>1</sub>	2.05	
<i>wR</i> <sub>2</sub>	5.11	
Goodness of fit on <i>F</i> <sup>2</sup>	1.090	

\*Second component of the crystal is related to the first component by the twin matrix [100 0̄10 001].

the *International Tables for Crystallography* (Wilson, 1992). In the crystal structure of hejtmanite, there are 3 groups of cation sites: *M*<sup>O</sup> sites of the O sheet, *M*<sup>H</sup> and *Si* sites of the H sheet, and peripheral *A*<sup>P</sup> sites which occur in the I block; site labelling is in accord with Sokolova (2006). Site-scattering values were refined for the *M*<sup>O</sup>(1–5) sites with the scattering curve of Mn, *M*<sup>H</sup>(1,2) sites (scattering curve of Ti) and *A*<sup>P</sup>(1,2) sites (scattering curve of Ba). For the H(1,2) atoms, the D (donor)–H distances were softly constrained to 0.98 Å. Final atom coordinates and anisotropic displacement parameters for hejtmanite are listed in Table 4, selected interatomic distances and angles are given in Table 5, refined site-scattering values and assigned site-populations for selected cation and anion sites are given in Table 6, bond-valence values for selected anions in Table 7 and details of hydrogen bonding in Table 8. A table of structure factors and CIF for hejtmanite have been deposited

with the Principal Editor of *Mineralogical Magazine* and are available from www.minersoc.org/pages/e\_journals/dep\_mat.html.

#### Topology of the structure

Hejtmanite is a TS-block mineral of Group II, Ti (+ Nb) = 2 apfu per (Si<sub>2</sub>O<sub>7</sub>)<sub>2</sub> (Sokolova, 2006).

The crystal structure of hejtmanite is a combination of a TS block and an I block (Fig. 1a). The TS block consists of HOH sheets. In the O sheet, there are five Mn-dominant [<sup>6</sup>]*M*<sup>O</sup>(1–5) sites, with <*M*<sup>O</sup>–φ> = 2.198 Å (φ = O, OH) (Tables 5, 6, Fig. 1b). Five *M*<sup>O</sup> sites ideally give Mn<sub>4</sub> apfu (Table 6). In the H sheet, the two [<sup>6</sup>]*M*<sup>H</sup>(1,2) sites are occupied mainly by Ti and minor Nb and Zr, ideally giving Ti<sub>2</sub> apfu, with <*M*<sup>H</sup>–φ> = 1.962 Å (φ = O, F) and four [<sup>4</sup>]*Si* sites are occupied solely by Si, with <Si–O> = 1.625 Å (Tables 5, 6). The *M*<sup>H</sup> octahedra and

## THE CRYSTAL STRUCTURE OF HEJTMANITE

TABLE 4. Atom coordinates and anisotropic displacement parameters ( $\text{\AA}^2$ ) for hejtmomite.

Atom	<i>x</i>	<i>y</i>	<i>z</i>	<i>U</i> <sup>11</sup>	<i>U</i> <sup>22</sup>	<i>U</i> <sup>33</sup>	<i>U</i> <sup>23</sup>	<i>U</i> <sup>13</sup>	<i>U</i> <sup>12</sup>	<i>U</i> <sub>eq</sub>
M <sup>O</sup> (1)	0	0	0	0.007(5)	0.0103(5)	0.0145(5)	-0.0002(4)	0.0048(4)	0.0008(4)	0.0104(3)
M <sup>O</sup> (2)	0.24447(4)	0.12358(6)	-0.01128(4)	0.0082(2)	0.0102(2)	0.0121(2)	0.0003(4)	-0.0011(3)	-0.0106(12)	0.0101(12)
M <sup>O</sup> (3)	0.25626(4)	0.87317(6)	0.00822(4)	0.0087(2)	0.0104(2)	0.0114(2)	-0.0002(4)	0.00394(15)	0.0001(4)	0.0109(12)
M <sup>O</sup> (4)	0.99575(5)	0.75166(3)	0.99334(5)	0.0084(5)	0.0123(4)	0.0164(5)	0.0036(3)	0.0026(3)	-0.0001(3)	0.0130(3)
M <sup>O</sup> (5)	0	0	0.0064(5)	0.0193(6)	0.0255(7)	0.0109(5)	0.0023(4)	0.0023(4)	0.0182(3)	0.0023(4)
M <sup>H</sup> (1)	0.46397(5)	0.60457(4)	0.71450(5)	0.0039(2)	0.0085(3)	0.0059(2)	0.0001(17)	0.00229(17)	0.00015(17)	0.00598(16)
M <sup>H</sup> (2)	0.53708(5)	0.85658(4)	0.288356(5)	0.0038(2)	0.0094(4)	0.0061(2)	0.00073(18)	0.00235(17)	0.00029(18)	0.00627(17)
Si(1)	0.28264(14)	0.01493(9)	0.24821(13)	0.0077(5)	0.0061(5)	0.0072(5)	-0.0002(4)	0.0018(4)	0.0010(4)	0.0073(3)
Si(2)	0.71633(14)	0.76433(9)	0.75030(13)	0.0064(5)	0.0085(5)	0.0069(5)	0.0004(4)	0.0031(4)	0.0003(4)	0.0071(2)
Si(3)	0.74114(14)	0.48385(9)	0.74999(13)	0.0069(5)	0.0066(5)	0.0069(5)	-0.0002(4)	0.0028(4)	-0.0004(4)	0.0067(2)
Si(4)	0.26032(14)	0.73678(9)	0.24669(13)	0.0085(5)	0.0077(5)	0.0073(5)	0.0008(4)	0.0029(4)	-0.0001(4)	0.0079(3)
A <sup>P</sup> (1)	0.61130(2)	0.62440(2)	0.46623(1)	0.00851(8)	0.0084(1)	0.00841(8)	0.00013(16)	0.00315(6)	0.00035(16)	0.00986(5)
A <sup>P</sup> (2)	0.38948(2)	0.87832(3)	0.53561(2)	0.00985(9)	0.03465(14)	0.01072(10)	-0.0004(2)	0.00416(7)	-0.0019(2)	0.01833(7)
A(1)	0.4168(3)	0.95191(19)	0.3214(2)	0.0104(11)	0.0170(13)	0.0123(12)	0.0008(11)	0.0052(9)	0.0042(10)	0.0130(5)
O(2)	0.50082(2)	0.50082(3)	0.3061(2)	0.0123(12)	0.0140(13)	0.0152(12)	-0.0008(11)	0.0102(10)	-0.0020(10)	0.0123(5)
O(3)	0.2192(4)	1.0000(3)	0.1006(3)	0.0085(14)	0.0152(15)	0.0039(15)	-0.0002(12)	-0.0001(11)	0.0003(11)	0.0099(7)
O(4)	0.65560(19)	0.87436(18)	0.72513(17)	0.0107(8)	0.0095(9)	0.0104(9)	0.0000(10)	0.0031(7)	-0.0011(10)	0.0105(4)
O(5)	0.6724(3)	0.7532(2)	0.3096(3)	0.0108(12)	0.0162(13)	0.0144(12)	0.0066(11)	0.0064(9)	0.0044(11)	0.0133(5)
O(6)	0.7838(4)	0.7504(2)	0.8986(4)	0.0099(14)	0.0083(14)	0.0107(16)	0.0006(12)	0.0048(12)	0.0006(11)	0.0094(7)
O(7)	0.5829(3)	0.69880(18)	0.6825(2)	0.0136(12)	0.0127(12)	0.0129(12)	-0.0016(10)	0.0069(9)	-0.0033(10)	0.0126(5)
O(8)	0.81866(3)	0.54787(18)	0.66829(3)	0.0112(12)	0.0147(13)	0.0145(12)	0.0000(11)	0.0062(9)	-0.0025(10)	0.0131(5)
O(9)	0.5806(2)	0.50058(19)	0.6939(2)	0.0077(11)	0.0156(13)	0.0137(12)	-0.0021(10)	0.0032(9)	0.0020(9)	0.0126(5)
O(10)	0.7975(4)	0.4969(3)	0.4969(3)	0.0106(15)	0.0143(15)	0.0053(15)	-0.0016(12)	0.0013(12)	0.0005(11)	0.0106(7)
O(11)	0.27786(19)	0.87280(19)	0.72202(17)	0.0112(8)	0.0086(9)	0.0118(9)	0.0007(10)	0.0049(7)	0.0002(10)	0.0104(4)
O(12)	0.2056(4)	0.7507(2)	0.101(4)	0.0096(15)	0.0090(14)	0.0103(16)	0.0003(12)	0.0051(12)	0.0001(11)	0.0092(7)
O(13)	0.4205(2)	0.75227(19)	0.3126(2)	0.0086(11)	0.0148(13)	0.0150(12)	0.00038(11)	0.0032(9)	-0.0000(10)	0.0132(5)
O(14)	0.3162(3)	0.69775(18)	0.6804(2)	0.0105(12)	0.0141(12)	0.01248	-0.0021(10)	0.0046(9)	0.0026(10)	0.0123(5)
X <sup>O</sup> <sub>M</sub> (1)	0.5347(2)	0.6161(3)	0.87959(19)	0.0094(9)	0.0158(14)	0.0096(9)	-0.0004(12)	0.0047(7)	-0.0016(11)	0.0113(5)
X <sup>O</sup> <sub>M</sub> (2)	0.4650(2)	0.8656(3)	0.12430(19)	0.0100(9)	0.0163(4)	0.0109(9)	-0.0020(12)	0.0040(7)	0.0000(12)	0.0123(5)
X <sup>A</sup> <sub>M</sub> (1)	-0.0432(2)	0.1243(3)	0.08664(18)	0.0135(9)	0.0118(10)	0.0106(9)	0.0008(15)	0.0043(7)	0.0013(16)	0.0120(4)
X <sup>O</sup> <sub>P</sub> (2)	0.45556(19)	0.1270(3)	0.07877(18)	0.0101(9)	0.0134(10)	0.0093(9)	-0.0002(16)	0.0031(7)	0.0003(16)	0.0111(4)
X <sup>A</sup> <sub>P</sub> (1)	0.611734(19)	0.40573(16)	0.47886(18)	0.0122(9)	0.0277(11)	0.0089(9)	-0.0012(7)	0.0040(7)	0.0048(8)	0.0162(4)
X <sup>M</sup> <sub>M</sub> (1)	0.61551(19)	0.85348(19)	0.48003(17)	0.0134(9)	0.0449(17)	0.0079(9)	0.0002(9)	0.0038(7)	0.0221(6)	0.0009(9)
H(1)	-0.003(3)	0.142(3)	0.1730(14)	0.01445*	0.01334*	0.01652(3)	0.01334*			
H(2)	0.494(3)	0.146(3)	0.1652(3)	0.01334*						

\*  $U_{\text{iso}}$ .

TABLE 5. Selected interatomic distances ( $\text{\AA}$ ) and angles ( $^\circ$ ) in hejtmanite.

$M^O(1)-X_A^O(1)$	2.133(4)	x2	$M^O(2)-X_A^O(2)$	2.104(2)	$M^O(3)-X_A^O(1)d$	2.129(2)
$M^O(1)-O(3)a$	2.194(4)	x2	$M^O(2)-X_M^O(1)b$	2.128(2)	$M^O(3)-X_M^O(2)$	2.137(2)
$M^O(1)-X_M^O(1)b$	2.262(3)	x2	$M^O(2)-O(6)b$	2.170(4)	$M^O(3)-O(3)$	2.174(4)
$\langle M^O(1)-\varphi \rangle$	2.196		$M^O(2)-O(10)b$	2.228(4)	$M^O(3)-O(12)$	2.192(4)
			$M^O(2)-O(3)a$	2.234(4)	$M^O(3)-O(12)e$	2.270(4)
			$M^O(2)-O(6)c$	2.275(4)	$M^O(3)-O(10)f$	2.284(4)
			$\langle M^O(2)-\varphi \rangle$	2.190	$M^O(3)-\varphi$	2.198
$M^O(4)-X_A^O(1)c$	2.107(4)		$M^O(5)-O(10)b$	2.044(4)	x2	
$M^O(4)-X_A^O(2)g$	2.118(4)		$M^O(5)-X_A^O(2)$	2.119(4)	x2	
$M^O(4)-O(6)$	2.118(4)		$M^O(5)-X_M^O(2)a$	2.479(3)	x2	
$M^O(4)-O(12)h$	2.123(4)		$\langle M^O(5)-\varphi \rangle$	2.214		
$M^O(4)-X_M^O(2)j$	2.270(3)					
$M^O(4)-X_M^O(1)i$	2.458(3)					
$\langle M^O(4)-\varphi \rangle$	2.199					
$M^H(1)-X_M^O(1)$	1.807(2)		$M^H(2)-X_M^O(2)$	1.796(2)		
$M^H(1)-O(7)$	1.954(3)		$M^H(2)-O(8)j$	1.961(3)	$Si(1)-O(2)k$	1.605(3)
$M^H(1)-O(14)$	1.960(3)		$M^H(2)-O(1)$	1.980(3)	$Si(1)-O(1)a$	1.622(3)
$M^H(1)-O(9)$	1.977(3)		$M^H(2)-O(5)$	1.982(3)	$Si(1)-O(3)a$	1.622(4)
$M^H(1)-O(2)c$	1.994(3)		$M^H(2)-O(13)$	1.990(3)	$Si(1)-O(4)c$	1.645(3)
$M^H(1)-X_M^P(1)c$	2.091(5)		$M^H(2)-X_M^P(2)$	2.088(2)	$\langle Si(1)-O \rangle$	1.624
$\langle M^H(1)-\varphi \rangle$	1.964		$\langle M^H(2)-\varphi \rangle$	1.960		
$Si(2)-O(5)j$	1.617(3)		$Si(3)-O(9)k$	1.609(3)	$Si(4)-O(13)$	1.607(3)
$Si(2)-O(7)$	1.623(3)		$Si(3)-O(8)r$	1.610(3)	$Si(4)-O(12)$	1.630(4)
$Si(2)-O(6)$	1.629(4)		$Si(3)-O(10)$	1.628(4)	$Si(4)-O(11)m$	1.633(3)
$Si(2)-O(4)$	1.633(3)		$Si(3)-O(11)l$	1.645(3)	$Si(4)-O(14)m$	1.636(3)
$\langle Si(2)-O \rangle$	1.626		$\langle Si(3)-O \rangle$	1.623	$\langle Si(4)-O \rangle$	1.627
$A^P(1)-X_M^P(2)j$	2.772(2)		$A^P(2)-X_M^P(1)n$	2.757(2)	$Si(1)c-O(4)-Si(2)$	136.6(1)
$A^P(1)-X_M^P(1)c$	2.792(2)		$A^P(2)-X_M^P(2)l$	2.759(2)	$Si(3)n-O(11)-Si(4)n$	136.4(1)
$A^P(1)-O(13)$	2.801(3)		$A^P(2)-O(1)$	2.836(3)	$\langle Si-O-Si \rangle$	136.5
$A^P(1)-O(2)$	2.803(3)		$A^P(2)-O(14)m$	2.860(3)		
$A^P(1)-O(9)c$	2.804(3)		$A^P(2)-O(11)$	2.871(2)		
$A^P(1)-O(5)$	2.830(3)		$A^P(2)-O(4)$	2.884(2)		
$A^P(1)-O(7)$	2.844(3)		$A^P(2)-O(1)o$	3.158(3)		
$A^P(1)-O(8)$	2.864(3)		$A^P(2)-O(8)n$	3.170(3)		
$A^P(1)-X_M^P(1)$	3.018(2)		$A^P(2)-O(13)$	3.265(3)		
$A^P(1)-X_M^P(2)$	3.163(3)		$A^P(2)-O(7)$	3.274(3)		
$A^P(1)-O(5)j$	3.235(3)		$A^P(2)-O(14)$	3.279(3)		
$A^P(1)-O(9)$	3.280(3)		$A^P(2)-O(2)n$	3.300(3)		
$\langle A^P(1)-\varphi \rangle$	2.934		$\langle A^P(2)-\varphi \rangle$	3.034		

a:  $x, y-1, z$ ; b:  $x-1/2, y-1/2, z-1$ ; c:  $-x+1, -y+1, -z+1$ ; d:  $-x, -y+1, -z$ ; e:  $-x+1/2, -y+3/2, -z$ ; f:  $x-1/2, y+1/2, z-1$ ; g:  $x+1/2, y+1/2, z+1$ ; h:  $x+1, y, z+1$ ; i:  $-x+3/2, -y+3/2, -z+2$ ; j:  $-x+3/2, -y+3/2, -z+1$ ; k:  $x-1/2, y-1/2, z$ ; l:  $x+1/2, y-1/2, z$ ; m:  $-x+1/2, -y+3/2, -z+1$ ; n:  $x-1/2, y+1/2, z$ ; o:  $-x+1, -y+2, -z+1$ .

$\text{Si}_2\text{O}_7$  groups constitute the H sheet (Fig. 1c). Two H sheets and the central O sheet link via common vertices of  $M^H$  octahedra and  $\text{Si}_2\text{O}_7$  groups with  $M^O$  octahedra to form the TS block. In Group II, the TS block exhibits linkage 2 where the  $\text{Si}_2\text{O}_7$  groups of two H sheets link to  $M^O$  octahedra adjacent along  $t_2$  ( $\parallel \mathbf{b}$  where  $b = 2t_2$ ) in the O sheet (Fig. 1a) as defined by Sokolova (2006). There are two

$[^{12}\text{Ba}]$ -dominant  $A^P(1,2)$  sites, with  $\langle A^P(1)-\varphi \rangle = 2.934 \text{ \AA}$  and  $\langle A^P(2)-\varphi \rangle = 3.034 \text{ \AA}$  ( $\varphi = \text{O}, \text{F}$ ). The two  $A^P$  sites ideally give  $\text{Ba}_2$  apfu (Table 6). In the crystal structure of hejtmanite, TS blocks link via a layer of Ba atoms which constitute the I block (Fig. 1a). The topology of the hejtmanite structure is identical to that of bafertisite (Cámarra *et al.*, 2015b).

## THE CRYSTAL STRUCTURE OF HEJTMANITE

TABLE 6. Refined site-scattering values and assigned site-populations for hejtmanite.

Site*	Refined site-scattering (epfu)	Assigned site-population (apfu)	Calculated site-scattering (epfu)	$\langle X-\varphi \rangle_{\text{obs.}}$ ** (Å)	Ideal composition (apfu)
Cations					
$M^O(1)$	12.70(6)	2.23 Mn + 1.65 Fe <sup>2+</sup>		2.196	Mn <sub>0.5</sub>
$M^O(2)$	25.94(7)	+ 0.04 Zn + 0.03 Mg + 0.05 □		2.190	Mn
$M^O(3)$	25.85(7)			2.198	Mn
$M^O(4)$	26.05(10)			2.199	Mn
$M^O(5)$	12.96(6)			2.214	Mn <sub>0.5</sub>
$\Sigma M^O(1-5)$	103.50	2.23 Mn + 1.65 Fe <sup>2+</sup> + 0.04 Zn + 0.03 Mg + 0.05 □	100.61		Mn <sub>4</sub>
$M^H(1)$	22.62(7)	1.88 Ti + 0.10 Nb + 0.02 Zr		1.964	Ti
$M^H(2)$	22.56(6)			1.960	Ti
$\Sigma M^H(1,2)$	45.18	1.88 Ti + 0.10 Nb + 0.02 Zr	46.26		Ti <sub>2</sub>
$[^{12}]A^P(1)$	55.21(10)	0.93 Ba + 0.02 Sr + 0.05 □	52.84	2.934	Ba
$[^{12}]A^P(2)$	53.48(10)	0.89 Ba + 0.07 K + 0.04 □	51.17	3.034	Ba
$\Sigma A^P(1,2)$	108.69	1.82 Ba + 0.07 K + 0.02 Sr + 0.09 □	104.01		Ba <sub>2</sub>
Anions					
$\Sigma X_M^O(1,2)$	2.00 O				O <sub>2</sub>
$\Sigma X_A^O(1,2)$	1.89 OH + 0.11 F				(OH) <sub>2</sub>
$\Sigma X_M^P(1,2)$	2.00 F				F <sub>2</sub>

\*Coordination number is given only for non-[6]-coordinated sites.

\*\*X = cation, φ = O, OH, F.

epfu – electrons per formula unit.

### Anion considerations

The O(1–14) atoms coordinate Si atoms of Si<sub>2</sub>O<sub>7</sub> groups, giving (Si<sub>2</sub>O<sub>7</sub>)<sub>2</sub> pfu. Two  $X_M^O(1,2)$  anions are bonded to one  $M^H$  (Ti) cation and three  $A^P$  (Ba) cations (Fig. 1d), they receive 0.84 and 0.82 vu (Table 7). We conclude that the  $X_M^P(1,2)$  anions are monovalent. The two  $X_M^P$  sites are coordinated by four cations and hence there is no space to accommodate

(Tables 5–7). Two  $X_M^P(1,2)$  anions are bonded to one  $M^H$  (Ti) cation and three  $A^P$  (Ba) cations (Fig. 1d), they receive 0.84 and 0.82 vu (Table 7). We conclude that the  $X_M^P(1,2)$  anions are monovalent. The two  $X_M^P$  sites are coordinated by four cations and hence there is no space to accommodate

TABLE 7. Bond-valence values\* for selected anions in hejtmanite.

Atom	$M^O(1)$	$M^O(2)$	$M^O(3)$	$M^O(4)$	$M^O(5)$	$M^H(1)$	$M^H(2)$	$A^P(1)$	$A^P(2)$	$\Sigma$
$X_M^O(1)$	0.28	0.39		0.17		1.00				1.84
$X_M^O(2)$			0.38	0.27	0.17		1.03			1.85
$[^3]X_A^O(1)$	0.38		0.39	0.41						1.18
$[^3]X_A^O(2)$		0.42		0.40	0.40					1.22
$X_M^P(1)$						0.34		0.18	0.19	0.84
$X_M^P(2)$						0.34		0.19	0.19	0.82
								0.13		
								0.10		

\*Bond-valence parameters (vu) are from Brown (1981); bond-valence values calculated for  $M^O$  = Mn;  $M^H$  = Ti;  $A^P$  = Ba; coordination numbers are shown for non-4-coordinated anions.

TABLE 8. Hydrogen bonding in hejtmanite.

D–H···A	D–H (Å)	H···A (Å)	D···A (Å)	∠ DHA (°)
X <sub>A</sub> <sup>O</sup> (1)OH–H(1)...O(5)a	0.98(1)	2.48(3)	3.285(4)	140(3)
X <sub>A</sub> <sup>O</sup> (1)OH–H(1)...O(9)a	0.98(1)	2.59(3)	3.339(4)	133(3)
X <sub>A</sub> <sup>O</sup> (2)OH–H(2)...O(11)b	0.98(1)	2.31(3)	2.931(3)	120(3)
X <sub>A</sub> <sup>O</sup> (2)OH–H(2)...O(4)b	0.98(1)	2.43(3)	2.976(3)	115(3)

a:  $x - \frac{1}{2}, y - \frac{1}{2}, z$ ; b:  $-x + 1, -y + 1, -z + 1$ .

the H atom of an OH group and a hydrogen bond at those sites. Therefore we assign F to the  $X_M^P(1,2)$  sites, and they give F<sub>2</sub> apfu (Table 6). Two X<sub>A</sub><sup>O</sup>(1,2) anions are bonded to three M<sup>O</sup> (Mn) cations, with incident valence sums of 1.18 and 1.22 vu (Table 7), hence they are monovalent anions. Chemical analysis gives 2.11 F apfu for hejtmanite (Table 2) and we assign 1.89 OH<sup>+</sup> [2.11–2.00 ( $X_M^P$ )<sub>2</sub>] = 0.11 F to the X<sub>A</sub><sup>O</sup>(1,2) sites, ideally (OH)<sub>2</sub> apfu (Table 6). The H(1,2) atoms are involved in weak hydrogen bonding with O atoms that belong to the H sheets (Table 8).

#### End-member formula

We write the end-member formula of hejtmanite as the sum of the groups of cation and anion sites: Ba<sub>2</sub>(A<sub>2</sub><sup>P</sup>) + Mn<sub>4</sub> (M<sub>4</sub><sup>O</sup>) + Ti<sub>2</sub> (M<sub>2</sub><sup>H</sup>) + (Si<sub>2</sub>O<sub>7</sub>)<sub>2</sub> + O<sub>2</sub> [( $X_M^P$ )<sub>2</sub>] + (OH)<sub>2</sub> [(X<sub>A</sub><sup>O</sup>)<sub>2</sub>] + F<sub>2</sub> [( $X_M^P$ )<sub>2</sub>] = Ba<sub>2</sub>Mn<sub>4</sub>Ti<sub>2</sub>(Si<sub>2</sub>O<sub>7</sub>)<sub>2</sub>O<sub>2</sub>(OH)<sub>2</sub>F<sub>2</sub>, Z = 4.

#### Basic TS-block structure

In the crystal structure of hejtmanite, (1) there is only one type of TS block of composition [Mn<sub>4</sub>Ti<sub>2</sub>(Si<sub>2</sub>O<sub>7</sub>)<sub>2</sub>O<sub>2</sub>(OH)<sub>2</sub>F<sub>2</sub>]<sup>4+</sup>; (2) the two H sheets of the TS block are identical; (3) there is only one type of I block of composition [Ba<sub>2</sub>]<sup>4+</sup>; and (4) there is only one type of self-linkage of TS blocks, via a layer of Ba atoms in the of the I block. Points (1)–(4) are in accord with the definition of a basic structure by Sokolova and Cámara (2013). The crystal structure of hejtmanite is of the B2(GII) structure type in accord with Sokolova and Cámara (2013).

#### On F in the Group-II TS-block structures

Ideal structural formulae for Group-II minerals hejtmanite and bafertisite (the bafertisite structure

type, B2); bobshannonite, perraultite and jinshajiangite (the perraultite structure type, B1), cámaraite (the D1 cámaraite structure type related to the bafertisite and perraultite structure types), yoshimuraite (B3) and bussenite (B4) are presented in Table 1. All minerals have basic structures except for cámaraite. In perraultite, jinshajiangite and bobshannonite, TS blocks connect via M<sup>H</sup>–X<sub>M</sub><sup>P</sup>–M<sup>H</sup> bridges as in the astrophyllite-group minerals (Cámaras *et al.*, 2010) and related naftisite, Na<sub>3</sub>Fe<sub>10</sub><sup>2+</sup>Ti<sub>2</sub>(Si<sub>6</sub>O<sub>17</sub>)<sub>2</sub>O<sub>2</sub>(OH)<sub>6</sub>F(H<sub>2</sub>O)<sub>2</sub> (Cámaras *et al.*, 2014b). The composition of an X<sub>M</sub><sup>P</sup> anion correlates with the composition of the M<sup>H</sup> cations: where M<sup>H</sup> sites are locally occupied by Nb (as in bobshannonite), the bridging anion is an O atom; where M<sup>H</sup> sites are occupied locally by Ti (as in perraultite and jinshajiangite), the bridging anion is a F atom (Table 1). A similar phenomenon was noted for astrophyllite-group minerals (*cf.* niobophyllite, Cámaras *et al.*, 2010). In most astrophyllite-group minerals, the X<sub>M</sub><sup>P</sup> anion is coordinated by six cations: two Ti or Nb (at the D site), two K (at the A site) and two Na (at the B site) and an OH group cannot/does not occur at the X<sub>M</sub><sup>P</sup> site as there is no room to accommodate an H atom and a hydrogen bond; where there is a vacancy at the A or B sites, OH groups occur at the X<sub>M</sub><sup>P</sup> site (Sokolova, 2012). In bafertisite and hejtmanite, TS blocks connect via a layer of Ba atoms in the I block. The F (X<sub>M</sub><sup>P</sup> site) atoms are apical anions of the M<sup>H</sup> (= Ti) cations and they are coordinated by four cations: Ti (M<sup>H</sup> site) and three Ba [A<sup>P</sup>(1,2) sites]. In bafertisite and hejtmanite, an OH group cannot occur at the X<sub>M</sub><sup>P</sup> site as there is no room to accommodate an H atom and a hydrogen bond. Hence F atoms and OH groups are ordered at the X<sub>M</sub><sup>P</sup> and X<sub>A</sub><sup>O</sup> sites, respectively.

Hejtmanite is related to cámaraite, ideally NaBa<sub>3</sub>Fe<sub>8</sub><sup>2+</sup>Ti<sub>4</sub>(Si<sub>2</sub>O<sub>7</sub>)<sub>4</sub>O<sub>4</sub>(OH)<sub>4</sub>F<sub>3</sub>. The derivative structure of cámaraite has one type of TS block, two types of I block, and TS blocks link to each other in

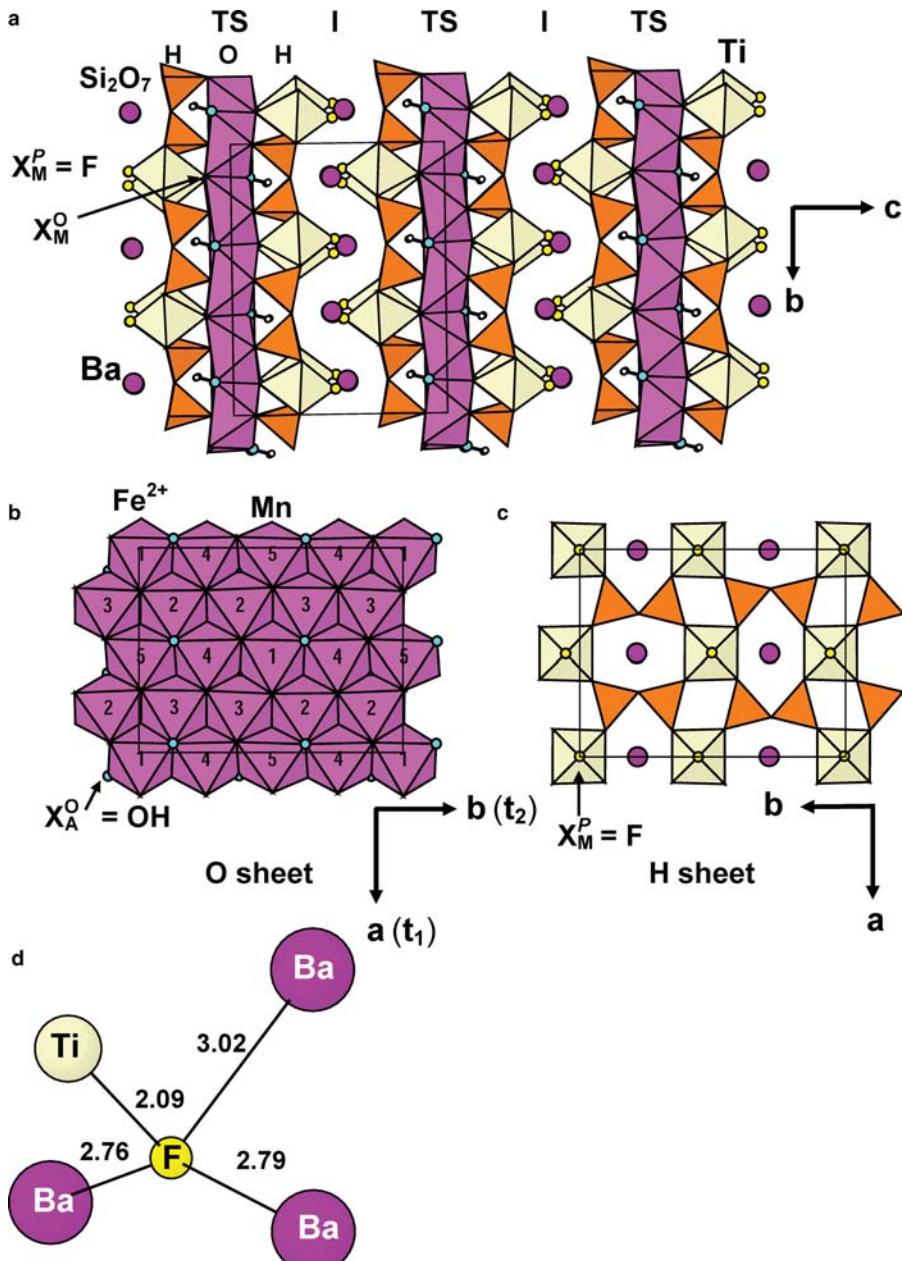


FIG. 1. A general view of the crystal structure of hejtmomite which consists of TS and I blocks (a) and the details of the structure: the close-packed O sheet of Mn-dominant  $\text{M}^{\text{O}}$  octahedra (b), the H sheet of  $\text{Ti}^{\text{H}}$ -dominant  $\text{M}^{\text{H}}$  octahedra and  $\text{Si}_2\text{O}_7$  groups (c), the F atom at the  $X_M^P$  site coordinated by the four cations (d).  $\text{SiO}_4$  tetrahedra are orange,  $\text{Ti}^{\text{H}}$ -dominant and Mn-dominant octahedra are yellow and magenta, respectively; Ba atoms at the  $A^P$  sites in the I block are shown as raspberry spheres; O and H atoms of OH groups at the  $X_A^O$  sites are shown as turquoise and small white spheres; F atoms at the  $X_M^P$  sites are shown as yellow spheres. The unit cell is shown by thin black lines.

two different ways. The structure of cámaraite can be built of structural fragments of minerals of the same group, jinshaijiangite and bafertsite. The bafertsite component of the cámaraite structure is topologically identical to the hejmanite structure. The general and ideal structural formulae of cámaraite are written as sums of the corresponding formulae of bafertsite and jinshaijiangite (Table 1).

## Summary

(1) Hejmanite, ideally  $\text{Ba}_2\text{Mn}_4\text{Ti}_2(\text{Si}_2\text{O}_7)_2\text{O}_2(\text{OH})_2\text{F}_2$ , is a Group-II TS-block mineral ( $\text{Ti} + \text{Nb} = 2$  apfu) in accord with Sokolova (2006). The crystal structure of hejmanite [ $a = 10.716(2)$ ,  $b = 13.795(3)$ ,  $c = 11.778(2)$  Å,  $\alpha = 90.07(3)$ ,  $\beta = 112.24(3)$ ,  $\gamma = 90.03(3)$ °,  $V = 1612(2)$  Å<sup>3</sup>, space group  $\bar{C}\bar{1}$ ] is of basic type [B2(GII)] and is an alternation of TS and I blocks of the composition  $[\text{Mn}_4\text{Ti}_2(\text{Si}_2\text{O}_7)_2\text{O}_2(\text{OH})_2\text{F}_2]^4-$  and  $[\text{Ba}_2]^{4+}$ , respectively. The crystal structure of hejmanite is of the same topology as that of baferite,  $\text{Ba}_2\text{Fe}_4^{2+}\text{Ti}_2(\text{Si}_2\text{O}_7)_2\text{O}_2(\text{OH})_2\text{F}_2$ .

(2) In the crystal structure of hejmanite, OH groups and F atoms are ordered at the  $X_A^O$  sites in the O sheet and  $X_M^P$  sites on the periphery of the TS block.

(3) The end-member formula of hejmanite is of the form  $A_2^P\text{M}_4^O\text{M}_2^H(\text{Si}_2\text{O}_7)_2(\text{X}^O)_4(\text{X}^P)_2$ :  $\text{Ba}_2\text{Mn}_4\text{Ti}_2(\text{Si}_2\text{O}_7)_2\text{O}_2(\text{OH})_2\text{F}_2$ ,  $Z = 4$  where  $A_2^P = \text{Ba}_2$ ,  $\text{M}_4^O = \text{Mn}_4$ ,  $\text{M}_2^H = \text{Ti}_2$ ,  $(\text{X}^O)_4 = (\text{X}_M^O)_2 + (\text{X}_A^O)_2 = \text{O}_2(\text{OH})_2$ ,  $(\text{X}_M^P)_2 = \text{F}_2$ .

## Acknowledgements

Mark Cooper is thanked for collecting single-crystal X-ray data for hejmanite. LAP acknowledges financial support by the grant 12-05-00911-a from the Russian Foundation for Basic Research; FC acknowledges financial support by the grant Ricerca Locale 2014, Università di Torino; FC and ES were supported by a Canada Research Chair in Crystallography and Mineralogy and by a Discovery grant from the Natural Sciences and Engineering Research Council of Canada and by Innovation Grants from the Canada Foundation for Innovation to FCH. We are grateful to Associate Editor Mark Welch and Reviewer Tony Kampf for useful comments.

## References

- Aksenov, S.M., Rastsvetaeva, R.K. and Chukanov, N.V. (2014) The crystal structure of emmerichite  $\text{Ba}_2\text{Na}_3\text{Fe}^{3+}\text{Ti}_2(\text{Si}_2\text{O}_7)_2\text{O}_2\text{F}_2$ , a new lamprophyllite-group mineral. *Zeitschrift für Kristallographie*, **229**, 1–7.
- Brown, I.D. (1981) The bond valence method: an empirical approach to chemical structure and bonding. Pp. 1–30 in: *Structure and Bonding in Crystals II* (M. O’Keeffe and A. Navrotsky, editors). Academic Press, New York.
- Cámaras, F., Sokolova, E. and Nieto, F. (2009) Cámarasite,  $\text{Ba}_3\text{NaTi}_4(\text{Fe}^{2+},\text{Mn})_8(\text{Si}_2\text{O}_7)_4\text{O}_4(\text{OH},\text{F})_7$ . II. The crystal structure and crystal chemistry of a new group-II Ti-disilicate mineral. *Mineralogical Magazine*, **73**, 855–870.
- Cámaras, F., Sokolova, E., Abdu, Y. and Hawthorne, F.C. (2010) The crystal structures of niobophyllite, kupletskite-(Cs) and Sn-rich astrophyllite; revisions to the crystal chemistry of the astrophyllite-group minerals. *The Canadian Mineralogist*, **48**, 1–16.
- Cámaras, F., Sokolova, E., Abdu, Y.A., Hawthorne, F.C. and Khomyakov, A.P. (2013) Kolskyite,  $(\text{Ca}\square)\text{Na}_2\text{Ti}_4(\text{Si}_2\text{O}_7)_2\text{O}_4(\text{H}_2\text{O})_7$ , a Group-IV Ti-disilicate mineral from the Khibiny alkaline massif, Kola Peninsula, Russia: description and crystal structure. *The Canadian Mineralogist*, **51**, 921–936.
- Cámaras, F., Sokolova, E., Abdu, Y.A. and Hawthorne, F.C. (2014a) Saamite,  $\text{Ba}\square\text{TiNbNa}_3\text{Ti}(\text{Si}_2\text{O}_7)_2\text{O}_2(\text{OH})_2(\text{H}_2\text{O})_2$ , a Group-III Ti-disilicate mineral from the Khibiny alkaline massif, Kola Peninsula, Russia: description and crystal structure. *The Canadian Mineralogist*, **52**, 745–761.
- Cámaras, F., Sokolova, E., Abdu, Y.A. and Hawthorne, F.C. (2014b) Nafertsite,  $\text{Na}_3\text{Fe}^{2+}_{10}\text{Ti}_2(\text{Si}_6\text{O}_{17})_2\text{O}_2(\text{OH})_6\text{F}(\text{H}_2\text{O})_2$ , from Mt. Kukisvumchorr, Khibiny alkaline massif, Kola peninsula, Russia: Refinement of the crystal structure and revision of the chemical formula. *European Journal of Mineralogy*, **26**, 689–700.
- Cámaras, F., Sokolova, E., Abdu, Y.A., Hawthorne, F.C., Charrier, T., Dorcet, V. and Carpentier, J.-F. (2015a) Fogoite-(Y), IMA 2014-098. CNMNC Newsletter No. 24, April 2015, page 250; *Mineralogical Magazine*, **79**, 247–251.
- Cámaras, F., Sokolova, E., Abdu, Y.A. and Pautov, L.A. (2015b) From structure topology to chemical composition. UIX. Titanium silicates: revision of the crystal structure and chemical formula of bafertsite,  $\text{Ba}_2\text{Fe}_4^{2+}\text{Ti}_2(\text{Si}_2\text{O}_7)_2\text{O}_2(\text{OH})_2\text{F}_2$ , a Group-II TS-block mineral. *The Canadian Mineralogist* (accepted).
- Cámaras, F., Sokolova, E. and Hawthorne, F.C. (2016) From structure topology to chemical composition. XXII. Titanium silicates: revision of the crystal structure of jinshaijiangite,  $\text{NaBaFe}_4^{2+}\text{Ti}_2(\text{Si}_2\text{O}_7)_2\text{O}_2(\text{OH})_2\text{F}$ , a Group-II TS-block mineral. *The Canadian Mineralogist* (accepted).
- Guan, Ya.S., Simonov, V.I. and Belov, N.V. (1963) Crystal structure of bafertsite,  $\text{BaFe}_2\text{TiO}[\text{Si}_2\text{O}_7](\text{OH})_2$ . *Doklady Akademii Nauk SSSR*, **149**, 1416–1419 [in Russian].

- McDonald, A.M., Grice, J.D. and Chao, G.Y. (2000) The crystal structure of yoshimuraite, a layered Ba-Mn-Ti silicophosphate. *The Canadian Mineralogist*, **38**, 649–656.
- Minerals. Handbook. Silicates (1996) IV(3) (additions to volumes III and IV), p. 132, Nauka, Moscow [in Russian].
- Peng Zhizhong and Shen Jinchuan (1963) Crystal structure of bafertisite. *Kexue Tongbao*, **14**, 66–68 [in Chinese].
- Pouchou, J.L. and Pichoir, F. (1985) "PAP" ( $\phi\phi Z$ ) procedure for improved quantitative microanalysis. Pp. 104–106 in: *Microbeam Analysis* (J.T. Armstrong, editor). San Francisco Press, San Francisco, California, USA.
- Rastsvetaeva, R.K., Tamazyan, R.A., Sokolova, E.V. and Belakovskii, D.I. (1991) Crystal structures of two modifications of natural Ba, Mn-titanosilicate. *Soviet Physics Crystallography*, **36**, 186–189.
- Rastsvetaeva, R.K., Eskova, E.M., Dusmatov, V.D., Chukanov, N.V. and Schneider, F. (2008) Surkhobite: revalidation and redefinition with the new formula,  $(Ba,K)_2CaNa(Mn,Fe^{2+},Fe^{3+})_8Ti_4(Si_2O_7)_4O_4(F,OH,O)_6$ . *European Journal of Mineralogy*, **20**, 289–295.
- Semenov, E.I. and Zhang Peishan (1959) New mineral – bafertisite. *Science Record. New Ser. Mineralogy*, **III** (12), 652–655 [in Russian].
- Sheldrick, G.M. (2008) A short history of SHELX. *Acta Crystallographica*, **A64**, 112–122.
- Sokolova, E. (2006) From structure topology to chemical composition. I. Structural hierarchy and stereochemistry in titanium disilicate minerals. *The Canadian Mineralogist*, **44**, 1273–1330.
- Sokolova, E. (2012) Further developments in the structure topology of the astrophyllite-group minerals. *Mineralogical Magazine*, **76**, 863–882.
- Sokolova, E. and Cámara, F. (2013) From structure topology to chemical composition. XVI. New developments in the crystal chemistry and prediction of new structure topologies for titanium disilicate minerals with the TS block. *The Canadian Mineralogist*, **51**, 861–891.
- Sokolova, E.V., Egorov-Tismenko, Yu.K., Pautov, L.A. and Belakovskii, D.I. (1989) On the crystal structure of a new Ba-titanosilicate,  $BaMn_2TiO[Si_2O_7](OH)_2$  – a member of the homologous series seidozerite–nacaphite. *Zapiski Vsesoyuznogo Mineralogicheskogo Obshchestva*, **118**, 81–84 [in Russian].
- Sokolova, E., Abdu, Y.A., Hawthorne, F.C., Genovesi, A., Cámara, F. and Khomyakov, A.P. (2015a) From structure topology to chemical composition. XVIII. Titanium silicates: revision of the crystal structure and chemical formula of betalomonosovite, a Group-IV TS-block mineral from the Lovozero alkaline massif, Kola Peninsula, Russia. *The Canadian Mineralogist*, **53**, 401–428.
- Sokolova, E., Cámara, F., Abdu, Y.A., Hawthorne, F.C., Horváth, L. and Pfenniger-Horváth, E. (2015b) Bobshannonite,  $Na_2KBa(Mn,Na)_8(Nb,Ti)_4(Si_2O_7)_4O_4(OH)_4(O,F)_2$ , a new TS-block mineral from Mont Saint-Hilaire, Québec, Canada: Description and crystal structure. *Mineralogical Magazine*, **79**, 1791–1811.
- Vrána, S., Rieder, M. and Gunter, M.E. (1992) Hejtmomite, a manganese-dominant analogue of bafertisite, a new mineral. *European Journal of Mineralogy*, **4**, 35–43.
- Wilson, A.J.C. (editor) (1992) *International Tables for Crystallography. Volume C: Mathematical, Physical and Chemical Tables*. Kluwer Academic Publishers, Dordrecht, The Netherlands.
- Yamnova, N.A., Egorov-Tismenko, Yu.K. and Pekov, I.V. (1998) Crystal structure of perraaultite from the coastal region of the Sea of Azov. *Crystallography Reports*, **43**, 401–410.
- Zhou, H., Rastsvetaeva, R.K., Khomyakov, A.P., Ma, Z. and Shi, N. (2002) Crystal structure of new micalike titanosilicate–bussenite,  $Na_2Ba_2Fe^{2+}[TiSi_2O_7][CO_3]O(OH)(H_2O)F$ . *Crystallography Reports*, **47**, 43–46.